

1 July 2026

## Beacon receives Final RC Drilling Results for Iguana Resource Definition Program

---

### Highlights

- **Beacon has received assay results for the final 195 RC holes. Key intercepts include the following:**
  - 24 metres @ 8.76 g/t gold from 91 metres (26IGRD0795)
    - Including 1 metre @ **81.20 g/t** gold from 100 metres
    - Including 1 metre @ **61.00 g/t** gold from 101 metres
  - 20 metres @ 9.90 g/t gold from 23 metres (26IGRD0765)
    - Including 1 metre @ **65.40 g/t** gold from 26 metres
  - 15 metres @ 12.06 g/t gold from 34 metres (26IGRD0732)
    - Including 1 metre @ **134.00 g/t** gold from 38 metres
  - 3 metres @ 56.73 g/t gold from 123 metres (26IGRD0658)
    - Including 1 metre @ **154.00 g/t** gold from 123 metres
  - 23 metres @ 7.34 g/t gold from 3 metres (26IGRD0766)
    - Including 1 metre @ **20.6 g/t** gold from 3 metres
  - 8 metres @ 18.03 g/t gold from 158 metres (26IGRD0611)
    - Including 1 metre @ **86.50 g/t** gold from 160 metres
  - 13 metres @ 8.84 g/t gold from 103 metres (26IGRD0761)
    - Including 1 metre @ **88.70 g/t** gold from 112 metres
  - 26 metres @ 4.26 g/t gold from 36 metres (26IGRD0744)
    - Including 1 metre @ **83.90 g/t** gold from 60 metres
- **Beacon has now received and validated all RC drill results from the 133,000m Resource Definition Drill program**
- **The program was the largest drill program carried out by Beacon and will provide an indicated resource down to the 360mRL of the Iguana orebody**
- **Entech Pty Ltd is currently finalising the Resource Update, to be released Q1 FY2027**



**Figure 1:** Iguana Pit on 22 June 2026.

**Beacon Minerals Executive Chairman and Managing Director Graham McGarry commented:**

“The Iguana Resource Definition drill program has been very successful for Beacon and laid a strong foundation for the Beacon’s ongoing mining and milling operations.

“Despite the large-scale drilling effort, the Iguana deposit remains open at depth, and to the south providing further potential to grow this company defining asset beyond its current boundaries.

“The Company looks forward to releasing the Iguana Resource and Reserve update in the near future”

## Overview

Beacon Minerals Limited (ASX: BCN) (“Beacon Minerals” or “the Company”) is pleased to announce the final batch of assay results for the extensive FY2026 Resource Development drill program at Lady Ida – Iguana Deposit.

The Iguana deposit is a part of the Lady Ida Project, which sits on the inferred extension of the Ida Fault and is a part of the north-south striking Mount Ida Greenstone Belt. It is predominantly metamorphosed (upper greenschist-amphibolite facies) mafic and ultramafic rocks. The complex structural geology provides the space for mineralisation deposition. The mineralisation is controlled by structural and hydrothermal alteration.

On the deposit scale the depth of weathering increases significantly within shear zones and reaches depths of 90m in the centre of the deposit. Supergene gold enrichment is apparent from grade control drilling in the upper portion of the existing Jamaican Rock pit (mined by Delta Gold in 2000) where significantly higher grades were mined compared to the current resource model.


Recent Diamond Drilling has indicated two distinct “In situ” mineralisation styles within the Iguana deposit.

### Early Stage Mineralisation

- Dominant mineralisation style of the Iguana deposit
- Sulphide-rich gold mineralisation
- Quartz is notably absent

### Later Stage Mineralisation

- Quartz-Fuchsite mineralisation style locally includes coarse visible gold
- Relatively small percentage of Iguana’s mineralisation

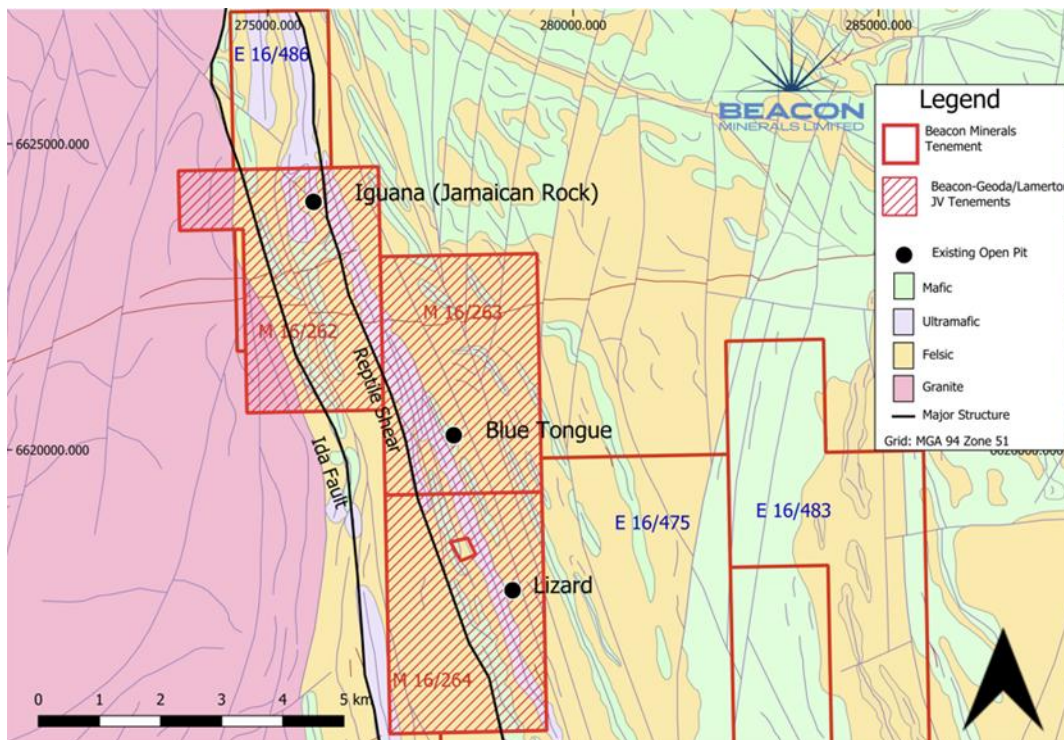

**Figure 2:** Iguana Local Geology and Tenements


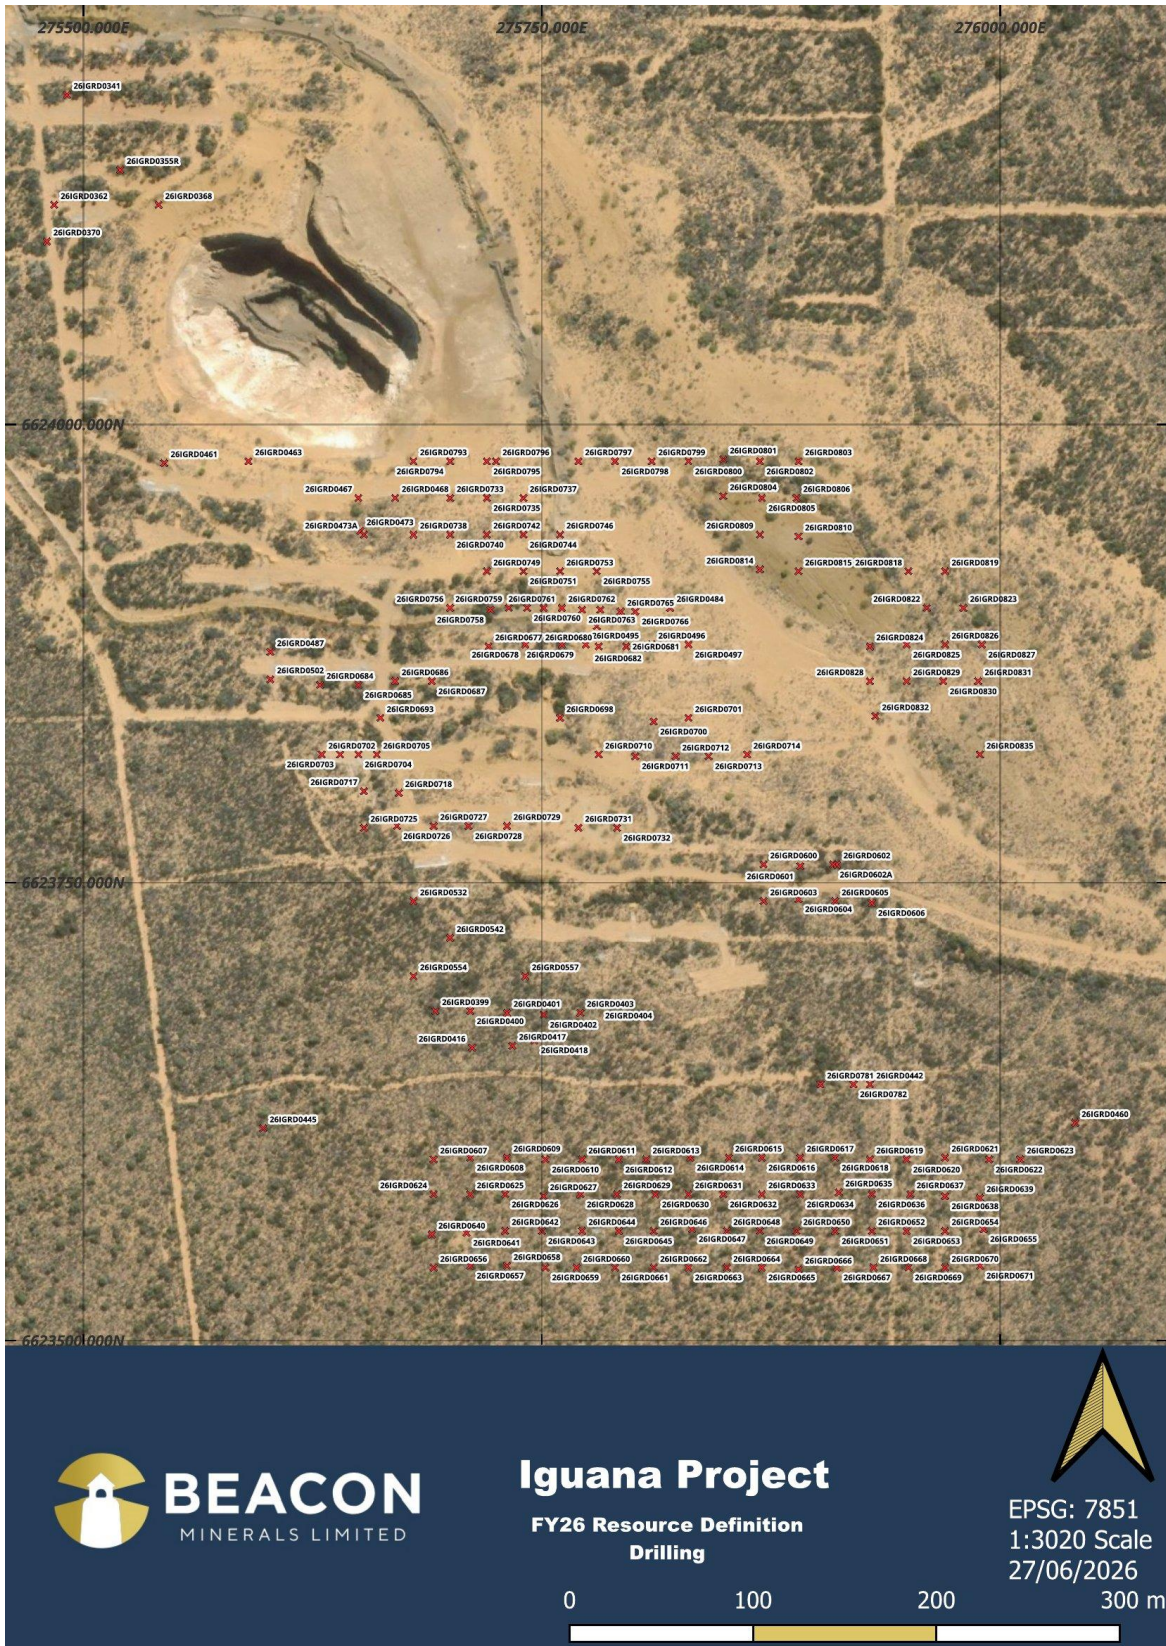


Figure 3: Collar Locations of Iguana Resource Development Drill Program

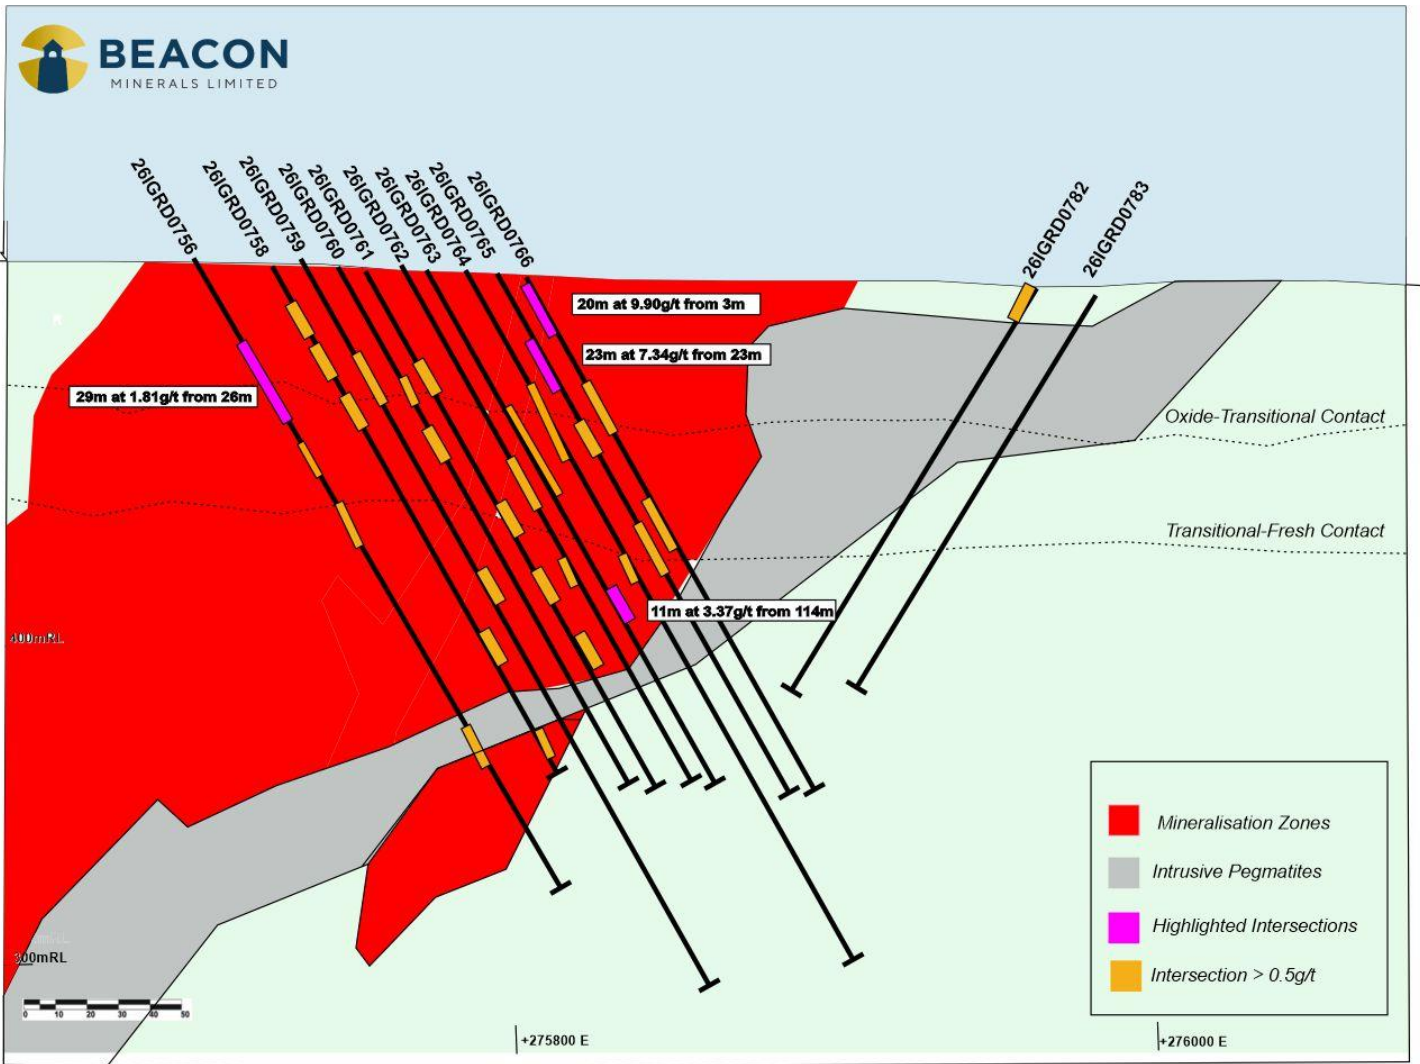


**Figure 4:** Cross Section of Iguana Resource Development Drill Program 662,390 Northing

### About the Lady Ida Project

The Lady Ida Project consist of M16/262 (the Iguana Deposit is located on M16/262), M16/263, M16/264, L15/224, L16/58, L16/62, L16/103, L16/142 and application L16/138 which is the ground the subject of the Earn-In, JV and Tenement Transfer Agreement between the Company, Beacon Mining Pty Ltd, Lamerton Pty Ltd and Geoda Pty Ltd.

For further details in relation to the Earn-In, JV and Tenement Transfer Agreement for the Lady Ida Project refer to ASX releases dated 6 December 2023 entitled “Beacon to Acquire an interest in the Lady Ida Gold Project” and 4 September 2024 “Lady Ida Completes and Appointment of New Director”.

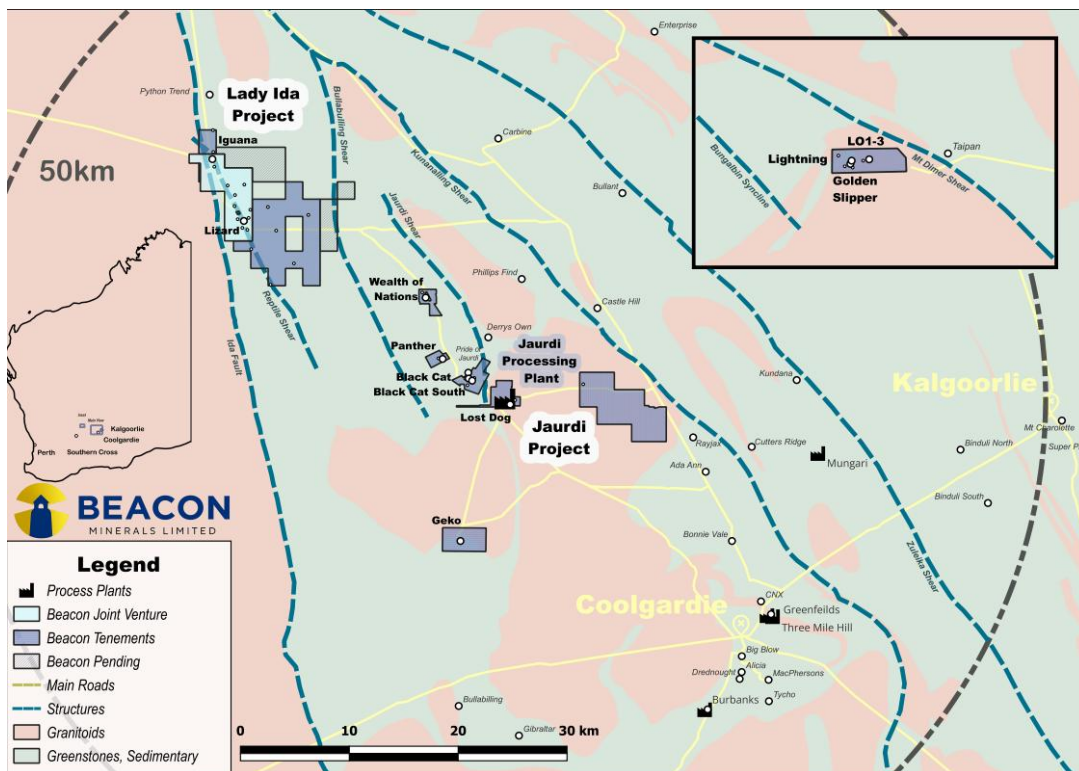

**Figure 5: Location of the Lady Ida Project (Iguana Deposit)**

Authorised for release by the Board of Beacon Minerals Limited.

**Graham McGarry**  
Managing Director/Chairman  
Beacon Minerals Limited  
+61 459 240 379

**Geoffrey Greenhill**  
Non-Executive Director  
Beacon Minerals Limited  
+61 419 991 713

**Competent Person Statement:**

The information in the report relating to the exploration results and targets have been compiled by Lachlan Kenna BSc (Hons) MAusIMM. Mr. Kenna has sufficient experience which is relevant to the style of mineralisation and types of deposits under consideration and to the activities being undertaken to qualify as a Competent Person as defined in the 2012 Edition of the 'Australasian Code for Reporting of Exploration Results, Mineral Resources and Ore Reserves'. Mr. Kenna is a consultant of Beacon Minerals Limited.

Mr Kenna consents to the inclusion in the report of the matters based on this information in the form and context in which it appears.

**Previously released exploration results**

Specific exploration results referred to in this announcement were originally reported in the following Company announcements in accordance with ASX Listing Rule 5.7:

Title	Date
Further Resource Definition Drilling Results Demonstrate Continued Mineralisation at Depth	12-Jan-26
First Batch of Iguana Resource Development Assays Received	09-Dec-25
Laterite Ore Reserve Statement - Iguana Deposit	23-Oct-25
Resource Development Drill Program Commences at Iguana Deposit	08-Oct-25
Final Batch of Iguana Grade Control Assays Received	22-Sep-25
Third Batch of Iguana Grade Control Assays Received	08-Sep-25
Second Batch of Assay Results at Iguana Deposit	18-Aug-25
Stage 2 Grade Control Program Completed at Lady Ida Iguana Deposit	11-Aug-25
Updated Laterite Mineral Resource for Iguana Deposit	5-Aug-25
Results of the Iguana Diamond Drill Program	29-Jul-25
Stage 2 Grade Control Program Commences at Lady Ida Iguana Deposit	22-Jul-25
Extensive Near Surface Laterite Mineralisation Identified at Iguana	16-Jul-25
Extensive Mineralisation Confirmed in First Pass Drill Program at Iguana	18-Jun-25
Stage 2 Laterite Drill Program completed at Lady Ida Iguana Deposit	4-Jun-25
Core Drilling commences at Lady Ida Iguana Deposit	21-Jan-25

The Company confirms that it is not aware of any information or data that materially affects the information included in the original announcements and the form and context in which the Competent Persons' findings are presented have not materially modified from the original market announcements.

**Forward Looking Statements:**

This ASX announcement (Announcement) has been prepared by Beacon Minerals Limited ("Beacon" or "the Company"). It should not be considered as an offer or invitation to subscribe for or purchase any securities in the Company or as an inducement to make an offer or invitation with respect to those securities. No agreement to subscribe for securities in the Company will be entered into on the basis of this Announcement.

This Announcement contains summary information about Beacon, its subsidiaries and their activities which is current as at the date of this Announcement. The information in this Announcement is of a general nature and does not purport to be complete nor does it contain all the information which a prospective investor may require in evaluating a possible investment in Beacon.

By its very nature exploration for minerals is a high risk business and is not suitable for certain investors. Beacon's securities are speculative. Potential investors should consult their stockbroker or financial advisor. There are a number of risks, both specific to Beacon and of a general nature which may affect the future operating and financial performance of Beacon and the value of an investment in Beacon including but not limited to economic conditions, stock market fluctuations, gold price movements, regional infrastructure constraints, timing of approvals from relevant authorities, regulatory risks, operational risks and reliance on key personnel.

Certain statements contained in this announcement, including information as to the future financial or operating performance of Beacon and its projects, are forward-looking statements that:

- may include, among other things, statements regarding targets, estimates and assumptions in respect of mineral reserves and mineral resources and anticipated grades and recovery rates, production and prices, recovery costs and results, capital expenditures, and are or may be based on assumptions and estimates related to future technical, economic, market, political, social and other conditions;
- are necessarily based upon a number of estimates and assumptions that, while considered reasonable by Beacon, are inherently subject to significant technical, business, economic, competitive, political and social uncertainties and contingencies; and,
- involve known and unknown risks and uncertainties that could cause actual events or results to differ materially from estimated or anticipated events or results reflected in such forward-looking statements.

Beacon disclaims any intent or obligation to update publicly any forward-looking statements, whether as a result of new information, future events or results or otherwise. The words 'believe', 'expect', 'anticipate', 'indicate', 'contemplate', 'target', 'plan', 'intends', 'continue', 'budget', 'estimate', 'may', 'will', 'schedule' and similar expressions identify forward-looking statements.

All forward looking statements made in this announcement are qualified by the foregoing cautionary statements. Investors are cautioned that forward-looking statements are not guarantees of future performance and accordingly investors are cautioned not to put undue reliance on forward-looking statements due to the inherent uncertainty therein. No verification: Although all reasonable care has been undertaken to ensure that the facts and opinions given in this Announcement are accurate, the information provided in this Announcement has not been independently verified.

#### **Disclaimer**

This ASX announcement (Announcement) has been prepared by Beacon Minerals Limited ("Beacon" or "the Company"). It should not be considered as an offer or invitation to subscribe for or purchase any securities in the Company or as an inducement to make an offer or invitation with respect to those securities. No agreement to subscribe for securities in the Company will be entered into on the basis of this Announcement.

This Announcement contains summary information about Beacon, its subsidiaries and their activities which is current as at the date of this Announcement. The information in this Announcement is of a general nature and does not purport to be complete nor does it contain all the information which a prospective investor may require in evaluating a possible investment in Beacon.

By its very nature exploration for minerals is a high risk business and is not suitable for certain investors. Beacon's securities are speculative. Potential investors should consult their stockbroker or financial advisor. There are a number of risks, both specific to Beacon and of a general nature which may affect the future operating and financial performance of Beacon and the value of an investment in Beacon including but not limited to economic conditions, stock market fluctuations, gold price movements, regional infrastructure constraints, timing of approvals from relevant authorities, regulatory risks, operational risks and reliance on key personnel.

Certain statements contained in this announcement, including information as to the future financial or operating performance of Beacon and its projects, are forward-looking statements that:

- may include, among other things, statements regarding targets, estimates and assumptions in respect of mineral reserves and mineral resources and anticipated grades and recovery rates, production and prices, recovery costs and results, capital expenditures, and are or may be based on assumptions and estimates related to future technical, economic, market, political, social and other conditions;
- are necessarily based upon a number of estimates and assumptions that, while considered reasonable by Beacon, are inherently subject to significant technical, business, economic, competitive, political and social uncertainties and contingencies; and,
- involve known and unknown risks and uncertainties that could cause actual events or results to differ materially from estimated or anticipated events or results reflected in such forward-looking statements.

Beacon disclaims any intent or obligation to update publicly any forward-looking statements, whether as a result of new information, future events or results or otherwise. The words 'believe', 'expect', 'anticipate', 'indicate', 'contemplate', 'target', 'plan', 'intends', 'continue', 'budget', 'estimate', 'may', 'will', 'schedule' and similar expressions identify forward-looking statements.

All forward looking statements made in this announcement are qualified by the foregoing cautionary statements. Investors are cautioned that forward-looking statements are not guarantees of future performance and accordingly investors are cautioned not to put undue reliance on forward-looking statements due to the inherent uncertainty therein.

No verification: Although all reasonable care has been undertaken to ensure that the facts and opinions given in this Announcement are accurate, the information provided in this Announcement has not been independently verified.

**Appendix 1: Significant Intercepts Table for the Iguana Resource Development Drill program**

All intervals of greater than 0.5 g/t gold with intervals of 3m samples only shown. The highly deformed nature of the deposit, and extensive mineralized envelop prevent the effective use or calculation of True Widths.

Hole No	From	To	Interval	Average Grade g/t	Gram Metres
26IGRD0655	0	1	1	0.77	0.77
26IGRD0735	0	1	1	0.61	0.61
26IGRD0742	0	1	1	0.55	0.55
26IGRD0749	0	1	1	0.76	0.76
26IGRD0753	0	3	3	4.27	12.80
26IGRD0755	0	1	1	0.50	0.50
26IGRD0758	0	6	6	1.49	8.95
26IGRD0759	0	2	2	0.93	1.86
26IGRD0760	0	7	7	0.63	4.44
26IGRD0761	0	5	5	0.87	4.34
26IGRD0763	0	4	4	0.98	3.92
26IGRD0798	0	2	2	1.25	2.49
26IGRD0809	0	1	1	0.52	0.52
26IGRD0814	0	1	1	0.56	0.56
26IGRD0824	0	1	1	0.55	0.55
26IGRD0473	1	2	1	1.25	1.25
26IGRD0682	1	2	1	1.05	1.05
26IGRD0711	1	2	1	0.81	0.81
26IGRD0718	1	2	1	0.58	0.58
26IGRD0726	1	2	1	0.84	0.84
26IGRD0751	1	4	3	1.21	3.63
26IGRD0794	1	2	1	2.01	2.01
26IGRD0797	1	2	1	0.54	0.54
26IGRD0799	1	3	2	1.46	2.92
26IGRD0818	1	3	2	2.19	4.38
26IGRD0822	1	4	3	0.82	2.46
26IGRD0368	2	4	2	1.23	2.45
26IGRD0484	2	3	1	0.54	0.54
26IGRD0487	2	3	1	0.65	0.65
26IGRD0679	2	4	2	0.58	1.16
26IGRD0680	2	3	1	3.72	3.72
26IGRD0681	2	3	1	0.82	0.82
26IGRD0710	2	3	1	0.54	0.54
26IGRD0762	2	4	2	0.66	1.32
26IGRD0765	2	4	2	1.31	2.62
26IGRD0800	2	4	2	1.52	3.03
26IGRD0801	2	3	1	0.80	0.80



26IGRD0802	2	3	1	0.54	0.54
26IGRD0803	2	3	1	1.31	1.31
26IGRD0804	2	4	2	0.72	1.43
26IGRD0810	2	4	2	0.71	1.42
26IGRD0814	2	3	1	0.52	0.52
26IGRD0827	2	3	1	0.85	0.85
26IGRD0831	2	4	2	2.09	4.18
26IGRD0677	3	4	1	0.84	0.84
26IGRD0678	3	4	1	0.55	0.55
26IGRD0680B	3	4	1	17.20	17.20
26IGRD0766	3	26	23	7.34	168.87
26IGRD0805	3	4	1	0.69	0.69
26IGRD0809	3	4	1	0.78	0.78
26IGRD0815	3	4	1	0.50	0.50
26IGRD0819	3	4	1	1.09	1.09
26IGRD0835	3	4	1	1.97	1.97
26IGRD0600	4	5	1	0.58	0.58
26IGRD0601	4	5	1	0.97	0.97
26IGRD0606	4	5	1	0.54	0.54
26IGRD0653	4	5	1	0.57	0.57
26IGRD0711	4	5	1	0.72	0.72
26IGRD0727	4	5	1	2.12	2.12
26IGRD0764	4	6	2	2.01	4.02
26IGRD0823	4	5	1	0.84	0.84
26IGRD0796	6	7	1	0.61	0.61
26IGRD0819	6	7	1	0.60	0.60
26IGRD0484	7	10	3	1.19	3.58
26IGRD0751	7	8	1	1.45	1.45
26IGRD0473	8	10	2	1.27	2.53
26IGRD0679	8	9	1	1.10	1.10
26IGRD0761	8	9	1	0.61	0.61
26IGRD0827	8	9	1	0.57	0.57
26IGRD0797	9	11	2	0.56	1.12
26IGRD0615	10	11	1	0.73	0.73
26IGRD0711	10	16	6	1.03	6.20
26IGRD0717	10	11	1	0.86	0.86
26IGRD0731	10	11	1	0.77	0.77
26IGRD0496	11	12	1	8.25	8.25
26IGRD0473A	12	33	21	3.25	68.15
26IGRD0662	12	13	1	0.74	0.74
26IGRD0678	12	13	1	0.76	0.76
26IGRD0712	12	23	11	1.36	14.92
26IGRD0735	12	14	2	0.63	1.26
26IGRD0753	12	14	2	0.80	1.60



26IGRD0758	12	22	10	2.64	26.43
26IGRD0473	13	31	18	3.47	62.40
26IGRD0755	14	16	2	0.89	1.78
26IGRD0496	15	23	8	1.26	10.09
26IGRD0731	15	18	3	0.57	1.72
26IGRD0762	15	17	2	0.63	1.25
26IGRD0763	15	16	1	0.71	0.71
26IGRD0795	15	16	1	0.53	0.53
26IGRD0797	15	16	1	0.59	0.59
26IGRD0798	15	16	1	0.82	0.82
26IGRD0484	16	34	18	5.55	99.81
26IGRD0764	16	17	1	0.57	0.57
26IGRD0612	17	18	1	0.56	0.56
26IGRD0814	17	18	1	0.64	0.64
26IGRD0368	18	19	1	1.49	1.49
26IGRD0700	18	25	7	0.82	5.71
26IGRD0717	18	21	3	4.85	14.55
26IGRD0749	18	19	1	0.97	0.97
26IGRD0795	18	24	6	0.78	4.70
26IGRD0468	19	20	1	0.50	0.50
26IGRD0617	19	21	2	6.48	12.96
26IGRD0677	19	21	2	0.95	1.89
26IGRD0737	19	21	2	0.61	1.22
26IGRD0755	19	20	1	0.60	0.60
26IGRD0467	20	24	4	0.54	2.15
26IGRD0798	21	22	1	0.90	0.90
26IGRD0755	22	34	12	1.85	22.14
26IGRD0487	23	24	1	1.15	1.15
26IGRD0682	23	24	1	1.50	1.50
26IGRD0687	23	24	1	1.41	1.41
26IGRD0763	23	24	1	0.64	0.64
26IGRD0765	23	43	20	9.90	198.02
26IGRD0368	24	31	7	0.66	4.62
26IGRD0416	24	34	10	0.91	9.05
26IGRD0679	24	26	2	0.57	1.14
26IGRD0710	24	25	1	0.53	0.53
26IGRD0746	24	50	26	3.21	83.35
26IGRD0753	24	27	3	1.76	5.28
26IGRD0355R	25	31	6	0.68	4.09
26IGRD0461	25	26	1	0.83	0.83
26IGRD0677	25	29	4	1.51	6.03
26IGRD0761	25	28	3	1.54	4.63
26IGRD0496	26	27	1	2.53	2.53
26IGRD0680	26	32	6	1.01	6.03



26IGRD0756	26	55	29	1.81	52.56
26IGRD0461	27	29	2	0.81	1.62
26IGRD0468	27	35	8	1.40	11.22
26IGRD0645	27	28	1	0.78	0.78
26IGRD0679	27	35	8	2.02	16.13
26IGRD0682	27	30	3	8.73	26.19
26IGRD0737	27	31	4	2.54	10.14
26IGRD0763	27	29	2	4.66	9.32
26IGRD0796	27	28	1	0.87	0.87
26IGRD0687	28	32	4	0.86	3.45
26IGRD0740	28	29	1	0.59	0.59
26IGRD0798	28	29	1	0.60	0.60
26IGRD0463	29	30	1	0.53	0.53
26IGRD0467	29	30	1	0.53	0.53
26IGRD0611	29	30	1	0.58	0.58
26IGRD0633	29	31	2	1.42	2.83
26IGRD0647	29	30	1	1.64	1.64
26IGRD0663	29	30	1	0.92	0.92
26IGRD0758	29	30	1	0.61	0.61
26IGRD0764	29	30	1	0.99	0.99
26IGRD0795	29	31	2	1.48	2.95
26IGRD0797	29	32	3	0.99	2.98
26IGRD0487	30	32	2	0.64	1.28
26IGRD0496	30	32	2	0.56	1.11
26IGRD0731	30	31	1	0.59	0.59
26IGRD0463	31	39	8	0.92	7.32
26IGRD0698	31	43	12	1.95	23.38
26IGRD0710	31	48	17	1.21	20.52
26IGRD0729	31	32	1	0.78	0.78
26IGRD0744	31	32	1	0.53	0.53
26IGRD0758	31	41	10	1.26	12.62
26IGRD0804	31	33	2	1.46	2.92
26IGRD0418	32	35	3	0.95	2.86
26IGRD0677	32	38	6	1.10	6.57
26IGRD0682	32	41	9	5.53	49.78
26IGRD0693	32	35	3	1.11	3.32
26IGRD0740	32	33	1	1.92	1.92
26IGRD0796	32	33	1	1.13	1.13
26IGRD0685	33	34	1	1.60	1.60
26IGRD0702	33	55	22	4.07	89.64
26IGRD0744	33	34	1	0.94	0.94
26IGRD0473	34	36	2	1.72	3.44
26IGRD0648	34	35	1	0.68	0.68
26IGRD0678	34	36	2	1.26	2.51



26IGRD0680B	34	35	1	0.51	0.51
26IGRD0705	34	35	1	0.90	0.90
26IGRD0711	34	50	16	1.67	26.65
26IGRD0729	34	78	44	1.32	58.09
26IGRD0732	34	49	15	12.06	180.90
26IGRD0751	34	37	3	1.08	3.23
26IGRD0759	34	42	8	1.14	9.11
26IGRD0760	34	35	1	1.42	1.42
26IGRD0763	34	36	2	1.31	2.62
26IGRD0401	35	36	1	0.70	0.70
26IGRD0761	35	36	1	1.64	1.64
26IGRD0795	35	38	3	0.56	1.68
26IGRD0814	35	38	3	3.26	9.79
26IGRD0404	36	37	1	1.68	1.68
26IGRD0632	36	40	4	1.01	4.02
26IGRD0648	36	40	4	1.82	7.26
26IGRD0687	36	37	1	0.60	0.60
26IGRD0731	36	48	12	2.12	25.42
26IGRD0742	36	38	2	0.60	1.19
26IGRD0484	37	40	3	0.57	1.71
26IGRD0502	37	38	1	0.66	0.66
26IGRD0735	37	38	1	0.55	0.55
26IGRD0740	37	38	1	0.53	0.53
26IGRD0766	37	55	18	2.56	46.12
26IGRD0797	37	38	1	0.68	0.68
26IGRD0355R	38	39	1	0.57	0.57
26IGRD0467	38	42	4	0.61	2.42
26IGRD0738	38	48	10	1.71	17.13
26IGRD0610	39	40	1	0.66	0.66
26IGRD0663	39	40	1	0.72	0.72
26IGRD0678	39	47	8	1.41	11.27
26IGRD0803	39	40	1	0.56	0.56
26IGRD0368	40	41	1	0.52	0.52
26IGRD0614	40	41	1	0.64	0.64
26IGRD0631	40	41	1	0.97	0.97
26IGRD0665	40	41	1	1.23	1.23
26IGRD0687	40	42	2	0.51	1.01
26IGRD0714	40	42	2	0.95	1.90
26IGRD0761	40	44	4	0.94	3.76
26IGRD0473A	41	52	11	1.00	11.02
26IGRD0487	41	42	1	0.70	0.70
26IGRD0613	41	42	1	0.81	0.81
26IGRD0677	41	50	9	1.17	10.50
26IGRD0679	41	43	2	2.92	5.84



26IGRD0749	41	49	8	1.41	11.26
26IGRD0760	41	49	8	0.71	5.65
26IGRD0764	41	66	25	2.70	67.50
26IGRD0814	41	45	4	2.50	10.01
26IGRD0368	42	43	1	1.12	1.12
26IGRD0473	42	48	6	5.22	31.33
26IGRD0614	42	46	4	2.24	8.94
26IGRD0661	42	44	2	0.87	1.73
26IGRD0663	42	43	1	0.78	0.78
26IGRD0664	42	43	1	1.17	1.17
26IGRD0704	42	43	1	0.77	0.77
26IGRD0740	42	46	4	0.95	3.81
26IGRD0742	42	43	1	0.59	0.59
26IGRD0755	42	45	3	0.84	2.52
26IGRD0804	42	43	1	0.82	0.82
26IGRD0355R	43	44	1	1.24	1.24
26IGRD0647	43	44	1	1.37	1.37
26IGRD0687	43	47	4	0.72	2.87
26IGRD0751	43	44	1	0.61	0.61
26IGRD0798	43	49	6	2.53	15.15
26IGRD0824	43	48	5	0.70	3.49
26IGRD0417	44	46	2	1.26	2.51
26IGRD0613	44	45	1	0.56	0.56
26IGRD0631	44	45	1	1.40	1.40
26IGRD0635	44	45	1	0.82	0.82
26IGRD0684	44	45	1	0.81	0.81
26IGRD0701	44	45	1	0.59	0.59
26IGRD0648	45	46	1	1.35	1.35
26IGRD0652	45	46	1	1.24	1.24
26IGRD0686	45	47	2	1.51	3.01
26IGRD0700	45	46	1	0.63	0.63
26IGRD0704	45	47	2	1.30	2.60
26IGRD0714	45	54	9	0.94	8.47
26IGRD0399	46	47	1	0.87	0.87
26IGRD0497	46	59	13	1.08	14.09
26IGRD0693	46	47	1	0.52	0.52
26IGRD0763	46	49	3	2.46	7.39
26IGRD0795	46	47	1	0.67	0.67
26IGRD0797	46	55	9	1.42	12.76
26IGRD0467	47	48	1	0.54	0.54
26IGRD0681	47	57	10	1.89	18.94
26IGRD0701	47	53	6	0.63	3.80
26IGRD0737	47	48	1	0.78	0.78
26IGRD0744	47	73	26	4.36	113.47



26IGRD0751	47	48	1	0.57	0.57
26IGRD0800	47	48	1	1.07	1.07
26IGRD0634	48	49	1	1.14	1.14
26IGRD0640	48	49	1	1.73	1.73
26IGRD0647	48	49	1	0.58	0.58
26IGRD0684	48	49	1	1.27	1.27
26IGRD0705	48	54	6	2.05	12.29
26IGRD0727	48	49	1	0.68	0.68
26IGRD0733	48	50	2	0.63	1.26
26IGRD0795	48	61	13	0.68	8.89
26IGRD0799	48	51	3	0.93	2.78
26IGRD0814	48	52	4	1.89	7.56
26IGRD0484	49	51	2	1.06	2.11
26IGRD0618	49	50	1	0.58	0.58
26IGRD0648	49	54	5	0.94	4.71
26IGRD0703	49	50	1	0.69	0.69
26IGRD0728	49	51	2	0.53	1.06
26IGRD0753	49	69	20	1.57	31.40
26IGRD0804	49	50	1	1.44	1.44
26IGRD0368	50	52	2	1.14	2.27
26IGRD0666	50	51	1	0.78	0.78
26IGRD0679	50	51	1	0.59	0.59
26IGRD0727	50	53	3	0.88	2.65
26IGRD0758	50	51	1	0.54	0.54
26IGRD0800	50	51	1	1.08	1.08
26IGRD0355R	51	55	4	1.23	4.93
26IGRD0496	51	53	2	2.65	5.30
26IGRD0628	51	57	6	13.10	78.57
26IGRD0678	51	58	7	1.93	13.54
26IGRD0682	51	55	4	1.11	4.45
26IGRD0809	51	56	5	1.05	5.25
26IGRD0461	52	57	5	3.37	16.84
26IGRD0615	52	53	1	1.22	1.22
26IGRD0679	52	53	1	0.79	0.79
26IGRD0684	52	53	1	0.77	0.77
26IGRD0693	52	55	3	0.54	1.63
26IGRD0698	52	53	1	0.58	0.58
26IGRD0704	52	55	3	0.68	2.04
26IGRD0728	52	53	1	0.80	0.80
26IGRD0758	52	53	1	0.59	0.59
26IGRD0763	52	72	20	2.39	47.80
26IGRD0631	53	55	2	0.59	1.18
26IGRD0677	53	54	1	0.56	0.56
26IGRD0687	53	56	3	3.38	10.14



26IGRD0737	53	55	2	1.34	2.68
26IGRD0755	53	60	7	2.81	19.69
26IGRD0765	53	55	2	0.66	1.32
26IGRD0794	53	55	2	2.29	4.58
26IGRD0810	53	54	1	0.66	0.66
26IGRD0417	54	55	1	2.02	2.02
26IGRD0636	54	55	1	0.65	0.65
26IGRD0646	54	55	1	2.12	2.12
26IGRD0652	54	55	1	0.73	0.73
26IGRD0684	54	55	1	2.05	2.05
26IGRD0698	54	56	2	0.69	1.38
26IGRD0718	54	57	3	0.80	2.39
26IGRD0746	54	59	5	0.51	2.57
26IGRD0758	54	55	1	0.83	0.83
26IGRD0802	54	55	1	0.63	0.63
26IGRD0473	55	57	2	1.28	2.56
26IGRD0502	55	59	4	1.27	5.06
26IGRD0617	55	56	1	1.78	1.78
26IGRD0679	55	64	9	1.10	9.94
26IGRD0711	55	57	2	2.11	4.21
26IGRD0728	55	56	1	0.78	0.78
26IGRD0759	55	56	1	0.51	0.51
26IGRD0761	55	59	4	1.44	5.75
26IGRD0796	55	56	1	0.59	0.59
26IGRD0799	55	56	1	0.93	0.93
26IGRD0814	55	61	6	1.02	6.12
26IGRD0815	55	62	7	0.64	4.50
26IGRD0463	56	60	4	0.76	3.02
26IGRD0647	56	57	1	1.67	1.67
26IGRD0664	56	57	1	0.51	0.51
26IGRD0677	56	61	5	0.93	4.64
26IGRD0701	56	65	9	1.81	16.25
26IGRD0735	56	67	11	1.76	19.31
26IGRD0368	57	58	1	0.98	0.98
26IGRD0370	57	71	14	2.65	37.12
26IGRD0615	57	61	4	2.11	8.45
26IGRD0616	57	58	1	1.82	1.82
26IGRD0726	57	59	2	1.90	3.80
26IGRD0765	57	58	1	3.06	3.06
26IGRD0600	58	59	1	0.50	0.50
26IGRD0601	58	59	1	0.79	0.79
26IGRD0631	58	60	2	0.53	1.06
26IGRD0633	58	61	3	6.26	18.77
26IGRD0682	58	60	2	0.72	1.43



26IGRD0749	58	59	1	1.20	1.20
26IGRD0794	58	65	7	2.09	14.66
26IGRD0799	58	62	4	0.77	3.09
26IGRD0355R	59	60	1	0.80	0.80
26IGRD0417	59	60	1	1.69	1.69
26IGRD0473A	59	60	1	0.50	0.50
26IGRD0618	59	61	2	0.59	1.18
26IGRD0686	59	68	9	1.13	10.17
26IGRD0693	59	61	2	0.68	1.36
26IGRD0698	59	64	5	3.93	19.66
26IGRD0702	59	63	4	0.72	2.88
26IGRD0703	59	61	2	0.80	1.59
26IGRD0710	59	63	4	1.26	5.05
26IGRD0714	59	60	1	0.67	0.67
26IGRD0717	59	65	6	0.69	4.11
26IGRD0733	59	60	1	6.69	6.69
26IGRD0756	59	60	1	0.56	0.56
26IGRD0759	59	60	1	0.70	0.70
26IGRD0760	59	60	1	0.79	0.79
26IGRD0649	60	61	1	0.62	0.62
26IGRD0718	60	61	1	0.59	0.59
26IGRD0742	60	61	1	0.68	0.68
26IGRD0362	61	69	8	1.84	14.74
26IGRD0368	61	70	9	1.03	9.28
26IGRD0473	61	68	7	8.15	57.08
26IGRD0631	61	64	3	1.51	4.52
26IGRD0704	61	62	1	0.50	0.50
26IGRD0714	61	62	1	0.79	0.79
26IGRD0793	61	62	1	2.30	2.30
26IGRD0341	62	63	1	2.32	2.32
26IGRD0497	62	63	1	0.59	0.59
26IGRD0662	62	63	1	0.51	0.51
26IGRD0664	62	63	1	0.72	0.72
26IGRD0726	62	64	2	0.66	1.31
26IGRD0756	62	67	5	0.55	2.73
26IGRD0765	62	63	1	0.99	0.99
26IGRD0417	63	64	1	0.67	0.67
26IGRD0681	63	64	1	0.81	0.81
26IGRD0687	63	74	11	3.12	34.32
26IGRD0759	63	64	1	0.59	0.59
26IGRD0403	64	65	1	0.54	0.54
26IGRD0468	64	67	3	0.97	2.92
26IGRD0497	64	70	6	1.15	6.91
26IGRD0677	64	72	8	1.92	15.37



26IGRD0678	64	66	2	0.94	1.88
26IGRD0680	64	65	1	0.55	0.55
26IGRD0685	64	67	3	0.58	1.75
26IGRD0714	64	65	1	0.60	0.60
26IGRD0467	65	66	1	0.60	0.60
26IGRD0473A	65	66	1	3.48	3.48
26IGRD0608	65	66	1	0.50	0.50
26IGRD0647	65	72	7	0.86	6.00
26IGRD0660	65	66	1	3.27	3.27
26IGRD0693	65	66	1	0.78	0.78
26IGRD0732	65	66	1	0.96	0.96
26IGRD0795	65	81	16	1.05	16.84
26IGRD0797	65	66	1	0.61	0.61
26IGRD0355R	66	67	1	0.66	0.66
26IGRD0442	66	67	1	2.63	2.63
26IGRD0461	66	67	1	3.61	3.61
26IGRD0628	66	67	1	0.51	0.51
26IGRD0680	66	72	6	1.96	11.76
26IGRD0760	66	69	3	0.71	2.14
26IGRD0793	66	73	7	3.14	21.95
26IGRD0404	67	68	1	0.50	0.50
26IGRD0633	67	68	1	1.25	1.25
26IGRD0726	67	69	2	4.35	8.69
26IGRD0746	67	68	1	0.54	0.54
26IGRD0814	67	68	1	0.56	0.56
26IGRD0832	67	68	1	1.23	1.23
26IGRD0463	68	77	9	3.21	28.93
26IGRD0496	68	69	1	0.63	0.63
26IGRD0628	68	69	1	2.49	2.49
26IGRD0702	68	69	1	0.54	0.54
26IGRD0714	68	70	2	1.16	2.32
26IGRD0766	68	69	1	1.49	1.49
26IGRD0467	69	74	5	1.15	5.74
26IGRD0710	69	74	5	1.62	8.12
26IGRD0738	69	75	6	0.91	5.43
26IGRD0740	69	70	1	0.51	0.51
26IGRD0751	69	72	3	2.10	6.30
26IGRD0755	69	74	5	0.83	4.14
26IGRD0799	69	75	6	0.94	5.66
26IGRD0800	69	70	1	0.50	0.50
26IGRD0815	69	70	1	1.56	1.56
26IGRD0496	70	93	23	1.94	44.53
26IGRD0629	70	71	1	12.20	12.20
26IGRD0649	70	71	1	89.40	89.40



26IGRD0613	71	73	2	0.98	1.96
26IGRD0686	71	72	1	0.94	0.94
26IGRD0693	71	72	1	0.71	0.71
26IGRD0698	71	78	7	0.68	4.75
26IGRD0701	71	72	1	0.51	0.51
26IGRD0355R	72	74	2	0.74	1.47
26IGRD0362	72	76	4	2.09	8.34
26IGRD0753	72	85	13	3.69	47.94
26IGRD0368	73	79	6	1.14	6.84
26IGRD0473	73	79	6	0.68	4.08
26IGRD0497	73	74	1	2.33	2.33
26IGRD0732	73	78	5	2.01	10.04
26IGRD0756	73	74	1	0.89	0.89
26IGRD0805	73	74	1	0.62	0.62
26IGRD0742	74	75	1	2.02	2.02
26IGRD0762	74	98	24	1.82	43.67
26IGRD0803	74	75	1	0.70	0.70
26IGRD0664	75	76	1	0.74	0.74
26IGRD0680	75	76	1	0.57	0.57
26IGRD0731	75	82	7	2.42	16.95
26IGRD0759	75	76	1	6.71	6.71
26IGRD0764	75	76	1	0.67	0.67
26IGRD0355R	76	78	2	0.58	1.16
26IGRD0400	76	77	1	0.64	0.64
26IGRD0617	76	77	1	0.57	0.57
26IGRD0677	76	77	1	1.33	1.33
26IGRD0680B	76	77	1	0.77	0.77
26IGRD0746	76	80	4	0.62	2.49
26IGRD0624	77	78	1	2.23	2.23
26IGRD0687	77	78	1	5.23	5.23
26IGRD0713	77	78	1	0.89	0.89
26IGRD0735	77	78	1	0.54	0.54
26IGRD0763	77	80	3	0.74	2.23
26IGRD0765	77	78	1	0.80	0.80
26IGRD0341	78	79	1	1.36	1.36
26IGRD0400	78	79	1	2.75	2.75
26IGRD0461	78	79	1	0.71	0.71
26IGRD0498	78	79	1	1.89	1.89
26IGRD0665	78	80	2	0.99	1.97
26IGRD0680	78	79	1	2.66	2.66
26IGRD0680B	78	80	2	2.76	5.52
26IGRD0682	78	79	1	0.63	0.63
26IGRD0693	78	81	3	2.31	6.94
26IGRD0710	78	80	2	0.87	1.74



26IGRD0744	78	79	1	1.02	1.02
26IGRD0766	78	93	15	1.82	27.26
26IGRD0793	78	79	1	0.60	0.60
26IGRD0799	78	91	13	0.91	11.80
26IGRD0832	78	79	1	0.77	0.77
26IGRD0497	79	80	1	3.63	3.63
26IGRD0614	79	80	1	1.01	1.01
26IGRD0714	79	80	1	0.68	0.68
26IGRD0677	80	83	3	33.31	99.93
26IGRD0685	80	82	2	2.97	5.93
26IGRD0717	80	81	1	2.20	2.20
26IGRD0463	81	82	1	2.74	2.74
26IGRD0678	81	84	3	1.04	3.11
26IGRD0682	81	83	2	1.37	2.74
26IGRD0687	81	82	1	0.57	0.57
26IGRD0701	81	85	4	0.85	3.38
26IGRD0714	81	82	1	2.62	2.62
26IGRD0735	81	82	1	0.56	0.56
26IGRD0751	81	86	5	0.97	4.87
26IGRD0800	81	82	1	1.15	1.15
26IGRD0368	82	88	6	0.83	5.00
26IGRD0659	82	83	1	1.55	1.55
26IGRD0713	82	97	15	1.77	26.59
26IGRD0727	82	83	1	0.58	0.58
26IGRD0749	82	83	1	0.52	0.52
26IGRD0828	82	83	1	0.53	0.53
26IGRD0634	83	84	1	4.12	4.12
26IGRD0680	83	84	1	0.52	0.52
26IGRD0687	83	91	8	2.33	18.67
26IGRD0700	83	84	1	0.68	0.68
26IGRD0746	83	84	1	2.87	2.87
26IGRD0814	83	84	1	0.62	0.62
26IGRD0717	84	85	1	0.67	0.67
26IGRD0473A	85	86	1	0.55	0.55
26IGRD0609	85	86	1	3.11	3.11
26IGRD0618	85	86	1	0.65	0.65
26IGRD0693	85	86	1	0.71	0.71
26IGRD0733	85	88	3	0.84	2.52
26IGRD0756	85	86	1	0.93	0.93
26IGRD0662	86	87	1	4.44	4.44
26IGRD0680	86	90	4	2.97	11.88
26IGRD0682	86	87	1	2.95	2.95
26IGRD0700	86	89	3	2.82	8.46
26IGRD0728	86	87	1	0.85	0.85



26IGRD0761	86	98	12	1.60	19.17
26IGRD0341	87	88	1	0.91	0.91
26IGRD0646	87	88	1	1.85	1.85
26IGRD0686	87	90	3	0.72	2.16
26IGRD0755	87	88	1	0.74	0.74
26IGRD0758	87	88	1	0.50	0.50
26IGRD0765	87	107	20	1.56	31.28
26IGRD0355R	88	89	1	13.50	13.50
26IGRD0463	88	90	2	1.53	3.06
26IGRD0701	88	93	5	3.15	15.73
26IGRD0702	88	90	2	1.58	3.16
26IGRD0728	88	89	1	0.62	0.62
26IGRD0732	88	89	1	2.81	2.81
26IGRD0403	89	90	1	0.55	0.55
26IGRD0650	89	90	1	0.78	0.78
26IGRD0680B	89	90	1	2.57	2.57
26IGRD0681	89	100	11	2.09	23.00
26IGRD0746	89	90	1	1.40	1.40
26IGRD0751	89	95	6	2.65	15.90
26IGRD0798	89	91	2	0.56	1.11
26IGRD0617	90	92	2	1.43	2.85
26IGRD0677	90	91	1	1.72	1.72
26IGRD0698	90	95	5	1.01	5.05
26IGRD0737	90	100	10	4.45	44.52
26IGRD0742	90	97	7	1.53	10.72
26IGRD0782	90	93	3	1.02	3.07
26IGRD0341	91	93	2	2.02	4.04
26IGRD0614	91	92	1	6.98	6.98
26IGRD0682	91	94	3	0.82	2.47
26IGRD0728	91	92	1	0.71	0.71
26IGRD0756	91	93	2	0.63	1.26
26IGRD0795	91	115	24	8.76	210.34
26IGRD0797	91	92	1	0.51	0.51
26IGRD0355R	92	95	3	0.91	2.73
26IGRD0468	92	93	1	2.16	2.16
26IGRD0473	92	94	2	1.03	2.06
26IGRD0484	92	93	1	1.51	1.51
26IGRD0612	92	93	1	1.24	1.24
26IGRD0685	92	95	3	0.84	2.52
26IGRD0798	92	93	1	1.63	1.63
26IGRD0368	93	96	3	0.72	2.17
26IGRD0666	93	94	1	0.66	0.66
26IGRD0758	93	94	1	0.76	0.76
26IGRD0610	94	95	1	1.52	1.52



26IGRD0643	94	97	3	1.45	4.34
26IGRD0703	94	95	1	0.51	0.51
26IGRD0733	94	96	2	2.35	4.69
26IGRD0746	94	95	1	1.44	1.44
26IGRD0763	94	97	3	2.30	6.90
26IGRD0473A	95	97	2	1.46	2.91
26IGRD0614	95	97	2	2.69	5.38
26IGRD0629	95	96	1	0.71	0.71
26IGRD0646	95	96	1	0.69	0.69
26IGRD0666	95	96	1	1.02	1.02
26IGRD0680	95	96	1	1.12	1.12
26IGRD0712	95	96	1	0.50	0.50
26IGRD0755	95	96	1	1.31	1.31
26IGRD0756	95	96	1	0.60	0.60
26IGRD0341	96	99	3	2.10	6.29
26IGRD0467	96	97	1	0.53	0.53
26IGRD0766	96	97	1	2.63	2.63
26IGRD0370	97	98	1	0.70	0.70
26IGRD0461	97	98	1	2.07	2.07
26IGRD0646	97	98	1	0.61	0.61
26IGRD0661	97	98	1	0.51	0.51
26IGRD0682	97	99	2	0.68	1.35
26IGRD0702	97	100	3	1.13	3.38
26IGRD0679	98	110	12	2.06	24.70
26IGRD0687	98	99	1	0.52	0.52
26IGRD0718	98	100	2	1.29	2.58
26IGRD0746	98	102	4	0.82	3.26
26IGRD0749	98	99	1	4.56	4.56
26IGRD0751	98	102	4	2.12	8.49
26IGRD0760	98	99	1	2.34	2.34
26IGRD0609	99	100	1	1.88	1.88
26IGRD0626	99	100	1	4.30	4.30
26IGRD0628	99	100	1	0.68	0.68
26IGRD0646	99	100	1	0.70	0.70
26IGRD0685	99	107	8	1.29	10.32
26IGRD0733	99	108	9	1.22	11.02
26IGRD0756	99	100	1	2.67	2.67
26IGRD0473A	100	101	1	0.50	0.50
26IGRD0629	100	101	1	2.95	2.95
26IGRD0645	100	103	3	0.71	2.14
26IGRD0755	100	102	2	5.86	11.71
26IGRD0797	100	104	4	1.27	5.08
26IGRD0800	100	108	8	0.79	6.29
26IGRD0643	101	104	3	0.80	2.39



26IGRD0684	101	104	3	3.34	10.02
26IGRD0687	101	105	4	1.93	7.70
26IGRD0700	101	102	1	1.10	1.10
26IGRD0712	101	104	3	1.13	3.40
26IGRD0727	101	108	7	1.47	10.30
26IGRD0731	101	108	7	1.33	9.30
26IGRD0753	101	102	1	0.81	0.81
26IGRD0764	101	112	11	1.86	20.47
26IGRD0496	102	103	1	0.77	0.77
26IGRD0624	102	103	1	0.79	0.79
26IGRD0640	102	103	1	0.61	0.61
26IGRD0646	102	103	1	0.63	0.63
26IGRD0682	102	106	4	1.00	4.00
26IGRD0701	102	106	4	1.08	4.30
26IGRD0713	102	103	1	0.56	0.56
26IGRD0728	102	103	1	0.55	0.55
26IGRD0463	103	121	18	1.41	25.35
26IGRD0487	103	104	1	0.56	0.56
26IGRD0609	103	104	1	0.54	0.54
26IGRD0658	103	104	1	0.52	0.52
26IGRD0681	103	122	19	1.45	27.63
26IGRD0760	103	113	10	1.89	18.85
26IGRD0761	103	116	13	8.84	114.86
26IGRD0355R	104	105	1	0.58	0.58
26IGRD0368	104	108	4	1.84	7.37
26IGRD0468	104	105	1	1.67	1.67
26IGRD0642	104	105	1	0.76	0.76
26IGRD0646	104	105	1	0.54	0.54
26IGRD0680B	104	106	2	1.55	3.10
26IGRD0740	104	105	1	0.69	0.69
26IGRD0798	104	105	1	3.48	3.48
26IGRD0416	105	107	2	0.72	1.44
26IGRD0487	105	106	1	0.82	0.82
26IGRD0693	105	108	3	2.89	8.68
26IGRD0751	105	106	1	1.53	1.53
26IGRD0762	105	112	7	0.68	4.79
26IGRD0362	106	107	1	0.59	0.59
26IGRD0542	106	107	1	0.60	0.60
26IGRD0660	106	107	1	0.56	0.56
26IGRD0700	106	112	6	1.36	8.14
26IGRD0728	106	107	1	0.70	0.70
26IGRD0749	106	115	9	1.12	10.06
26IGRD0753	106	110	4	0.95	3.78
26IGRD0759	106	107	1	0.53	0.53



26IGRD0763	106	107	1	0.59	0.59
26IGRD0487	108	109	1	2.25	2.25
26IGRD0740	108	109	1	1.93	1.93
26IGRD0744	108	110	2	0.56	1.12
26IGRD0756	108	109	1	0.52	0.52
26IGRD0341	109	110	1	0.73	0.73
26IGRD0473	109	118	9	1.12	10.05
26IGRD0660	109	111	2	0.74	1.47
26IGRD0678	109	111	2	3.64	7.28
26IGRD0680	109	110	1	5.79	5.79
26IGRD0680B	109	112	3	0.90	2.69
26IGRD0726	109	110	1	1.49	1.49
26IGRD0751	109	110	1	0.53	0.53
26IGRD0661	110	111	1	0.72	0.72
26IGRD0686	110	114	4	1.00	4.00
26IGRD0687	110	112	2	6.60	13.20
26IGRD0728	110	111	1	1.92	1.92
26IGRD0758	110	111	1	1.83	1.83
26IGRD0797	110	118	8	0.89	7.15
26IGRD0368	111	117	6	0.77	4.60
26IGRD0416	111	112	1	0.69	0.69
26IGRD0532	111	112	1	0.88	0.88
26IGRD0712	111	119	8	0.75	6.03
26IGRD0727	111	112	1	0.55	0.55
26IGRD0751	111	112	1	5.57	5.57
26IGRD0759	111	115	4	1.83	7.31
26IGRD0800	111	112	1	2.96	2.96
26IGRD0355R	112	113	1	0.91	0.91
26IGRD0685	112	114	2	0.59	1.17
26IGRD0740	112	116	4	1.18	4.70
26IGRD0744	112	113	1	0.61	0.61
26IGRD0765	112	114	2	1.30	2.60
26IGRD0700	113	121	8	1.14	9.12
26IGRD0461	114	115	1	0.81	0.81
26IGRD0678	114	129	15	1.90	28.52
26IGRD0726	114	122	8	0.68	5.47
26IGRD0727	114	130	16	1.32	21.19
26IGRD0728	114	116	2	1.12	2.23
26IGRD0733	114	117	3	1.21	3.64
26IGRD0753	114	122	8	0.91	7.28
26IGRD0755	114	115	1	1.48	1.48
26IGRD0763	114	125	11	3.37	37.09
26IGRD0798	114	115	1	0.59	0.59
26IGRD0403	115	122	7	0.65	4.54



26IGRD0781	115	116	1	0.76	0.76
26IGRD0800	115	116	1	0.51	0.51
26IGRD0679	116	117	1	0.55	0.55
26IGRD0682	116	117	1	2.07	2.07
26IGRD0685	116	117	1	0.55	0.55
26IGRD0687	116	124	8	1.57	12.53
26IGRD0693	116	117	1	0.90	0.90
26IGRD0702	116	118	2	1.33	2.66
26IGRD0718	116	117	1	2.21	2.21
26IGRD0744	116	119	3	1.59	4.78
26IGRD0758	116	118	2	6.16	12.31
26IGRD0762	116	117	1	0.75	0.75
26IGRD0341	117	127	10	2.77	27.71
26IGRD0461	117	129	12	1.26	15.13
26IGRD0473A	117	119	2	1.23	2.45
26IGRD0532	117	119	2	7.05	14.09
26IGRD0661	117	121	4	1.46	5.82
26IGRD0703	117	118	1	0.75	0.75
26IGRD0633	118	119	1	0.80	0.80
26IGRD0679	118	145	27	1.58	42.77
26IGRD0680	118	126	8	1.03	8.21
26IGRD0760	118	119	1	0.57	0.57
26IGRD0542	119	120	1	2.42	2.42
26IGRD0630	119	120	1	3.07	3.07
26IGRD0644	119	123	4	0.59	2.37
26IGRD0677	119	120	1	0.57	0.57
26IGRD0680B	119	120	1	5.37	5.37
26IGRD0684	119	120	1	0.82	0.82
26IGRD0685	119	122	3	1.37	4.11
26IGRD0703	119	121	2	1.16	2.32
26IGRD0728	119	122	3	0.87	2.61
26IGRD0800	119	126	7	2.76	19.30
26IGRD0810	119	120	1	0.59	0.59
26IGRD0355R	120	122	2	0.69	1.38
26IGRD0399	120	121	1	1.35	1.35
26IGRD0613	120	121	1	1.27	1.27
26IGRD0693	120	124	4	2.32	9.29
26IGRD0711	120	121	1	0.62	0.62
26IGRD0759	120	131	11	1.38	15.21
26IGRD0554	121	122	1	0.60	0.60
26IGRD0627	121	122	1	1.33	1.33
26IGRD0740	121	123	2	0.79	1.57
26IGRD0368	122	123	1	0.78	0.78
26IGRD0484	122	123	1	1.91	1.91



26IGRD0487	122	123	1	1.33	1.33
26IGRD0684	122	124	2	3.40	6.79
26IGRD0718	122	124	2	0.69	1.38
26IGRD0749	122	123	1	0.59	0.59
26IGRD0798	122	132	10	3.00	29.95
26IGRD0658	123	126	3	56.73	170.19
26IGRD0680B	123	132	9	1.68	15.15
26IGRD0686	123	129	6	7.82	46.91
26IGRD0760	123	124	1	0.56	0.56
26IGRD0764	123	126	3	0.87	2.61
26IGRD0758	124	125	1	1.33	1.33
26IGRD0418	125	126	1	0.63	0.63
26IGRD0463	125	126	1	0.59	0.59
26IGRD0554	125	127	2	1.05	2.10
26IGRD0610	125	126	1	1.85	1.85
26IGRD0685	125	129	4	1.22	4.88
26IGRD0711	125	136	11	2.75	30.21
26IGRD0781	125	126	1	2.60	2.60
26IGRD0473A	126	127	1	0.54	0.54
26IGRD0608	126	127	1	0.62	0.62
26IGRD0613	126	129	3	2.45	7.36
26IGRD0633	126	127	1	0.98	0.98
26IGRD0761	126	127	1	0.53	0.53
26IGRD0463	127	134	7	2.26	15.80
26IGRD0473	127	128	1	7.91	7.91
26IGRD0687	127	128	1	5.83	5.83
26IGRD0693	127	134	7	5.90	41.29
26IGRD0700	127	128	1	0.63	0.63
26IGRD0705	127	128	1	1.67	1.67
26IGRD0744	127	129	2	0.85	1.69
26IGRD0749	127	128	1	0.80	0.80
26IGRD0355R	128	129	1	0.82	0.82
26IGRD0467	128	129	1	1.11	1.11
26IGRD0473A	128	129	1	0.64	0.64
26IGRD0484	128	132	4	1.96	7.85
26IGRD0609	128	129	1	0.66	0.66
26IGRD0656	128	129	1	0.71	0.71
26IGRD0665	128	129	1	1.29	1.29
26IGRD0368	129	137	8	1.41	11.24
26IGRD0487	129	130	1	0.55	0.55
26IGRD0680	129	131	2	4.55	9.09
26IGRD0684	129	130	1	1.46	1.46
26IGRD0728	129	130	1	1.71	1.71
26IGRD0738	129	130	1	0.63	0.63



26IGRD0362	130	131	1	0.78	0.78
26IGRD0703	130	132	2	0.67	1.34
26IGRD0751	130	132	2	1.28	2.56
26IGRD0341	131	132	1	0.52	0.52
26IGRD0717	131	132	1	0.64	0.64
26IGRD0738	131	133	2	0.64	1.28
26IGRD0355R	132	138	6	1.33	8.00
26IGRD0657	132	133	1	1.31	1.31
26IGRD0686	132	133	1	1.68	1.68
26IGRD0710	132	133	1	0.59	0.59
26IGRD0761	132	134	2	1.73	3.45
26IGRD0762	132	133	1	1.46	1.46
26IGRD0766	132	133	1	2.01	2.01
26IGRD0802	132	133	1	0.63	0.63
26IGRD0532	133	134	1	0.73	0.73
26IGRD0608	133	134	1	1.42	1.42
26IGRD0626	133	134	1	0.87	0.87
26IGRD0685	133	152	19	0.89	16.94
26IGRD0727	133	135	2	3.27	6.53
26IGRD0733	133	142	9	0.82	7.35
26IGRD0740	133	134	1	0.85	0.85
26IGRD0758	133	134	1	1.09	1.09
26IGRD0763	133	135	2	0.59	1.17
26IGRD0487	134	153	19	4.55	86.50
26IGRD0612	134	138	4	3.38	13.51
26IGRD0643	134	135	1	1.12	1.12
26IGRD0644	134	142	8	1.32	10.52
26IGRD0678	134	135	1	1.35	1.35
26IGRD0680	134	135	1	0.59	0.59
26IGRD0684	134	136	2	1.30	2.59
26IGRD0746	134	136	2	0.92	1.83
26IGRD0753	134	135	1	4.77	4.77
26IGRD0502	135	137	2	1.13	2.25
26IGRD0554	135	139	4	0.89	3.57
26IGRD0702	135	137	2	0.87	1.73
26IGRD0705	135	137	2	1.12	2.23
26IGRD0742	135	136	1	0.94	0.94
26IGRD0461	136	144	8	2.15	17.23
26IGRD0682	136	137	1	0.67	0.67
26IGRD0710	136	139	3	2.85	8.55
26IGRD0729	136	142	6	0.99	5.94
26IGRD0370	137	138	1	5.20	5.20
26IGRD0467	137	139	2	2.24	4.48
26IGRD0484	137	138	1	5.03	5.03



26IGRD0608	137	138	1	0.54	0.54
26IGRD0686	137	139	2	1.32	2.64
26IGRD0726	137	138	1	0.51	0.51
26IGRD0758	137	139	2	7.59	15.18
26IGRD0797	137	138	1	0.52	0.52
26IGRD0362	138	146	8	1.81	14.51
26IGRD0629	138	139	1	1.28	1.28
26IGRD0678	138	142	4	1.15	4.60
26IGRD0687	138	139	1	9.75	9.75
26IGRD0718	138	139	1	0.76	0.76
26IGRD0727	138	147	9	7.93	71.38
26IGRD0341	139	140	1	0.65	0.65
26IGRD0628	139	141	2	2.52	5.04
26IGRD0711	139	140	1	0.60	0.60
26IGRD0402	140	145	5	2.70	13.48
26IGRD0468	140	144	4	1.77	7.09
26IGRD0643	140	141	1	0.50	0.50
26IGRD0680B	140	141	1	0.75	0.75
26IGRD0684	140	141	1	1.00	1.00
26IGRD0726	140	145	5	0.75	3.76
26IGRD0798	140	141	1	0.57	0.57
26IGRD0484	141	144	3	23.33	69.99
26IGRD0502	141	142	1	0.72	0.72
26IGRD0705	141	143	2	0.59	1.17
26IGRD0711	141	142	1	0.99	0.99
26IGRD0738	141	146	5	1.13	5.63
26IGRD0662	142	143	1	2.11	2.11
26IGRD0687	142	150	8	0.94	7.51
26IGRD0710	142	145	3	1.12	3.37
26IGRD0758	142	144	2	3.22	6.44
26IGRD0797	142	146	4	3.31	13.24
26IGRD0502	143	144	1	0.50	0.50
26IGRD0645	143	144	1	2.09	2.09
26IGRD0684	143	147	4	0.76	3.02
26IGRD0693	143	153	10	1.22	12.24
26IGRD0698	143	160	17	1.42	24.20
26IGRD0762	143	144	1	0.50	0.50
26IGRD0822	143	144	1	0.95	0.95
26IGRD0416	144	146	2	2.72	5.43
26IGRD0665	144	145	1	0.93	0.93
26IGRD0705	144	153	9	0.87	7.87
26IGRD0718	144	160	16	1.60	25.65
26IGRD0725	145	150	5	1.35	6.77
26IGRD0678	146	149	3	1.31	3.94



26IGRD0461	147	153	6	1.42	8.50
26IGRD0468	147	148	1	0.58	0.58
26IGRD0502	147	148	1	0.65	0.65
26IGRD0632	147	148	1	1.52	1.52
26IGRD0657	147	148	1	0.66	0.66
26IGRD0703	147	151	4	0.63	2.52
26IGRD0704	147	156	9	1.44	13.00
26IGRD0781	147	148	1	2.76	2.76
26IGRD0401	148	150	2	21.87	43.74
26IGRD0610	148	151	3	0.81	2.43
26IGRD0711	148	149	1	1.13	1.13
26IGRD0729	148	149	1	0.60	0.60
26IGRD0758	148	150	2	8.71	17.42
26IGRD0502	149	162	13	2.01	26.10
26IGRD0608	149	150	1	1.07	1.07
26IGRD0686	149	150	1	2.26	2.26
26IGRD0710	149	151	2	0.78	1.55
26IGRD0684	150	151	1	0.58	0.58
26IGRD0756	150	151	1	0.78	0.78
26IGRD0370	151	156	5	0.88	4.41
26IGRD0417	151	152	1	1.18	1.18
26IGRD0418	151	152	1	1.29	1.29
26IGRD0484	151	152	1	0.78	0.78
26IGRD0627	151	152	1	2.14	2.14
26IGRD0680	151	152	1	0.50	0.50
26IGRD0738	151	152	1	0.76	0.76
26IGRD0463	152	153	1	0.85	0.85
26IGRD0677	152	153	1	0.62	0.62
26IGRD0680B	152	153	1	0.98	0.98
26IGRD0749	152	156	4	1.93	7.71
26IGRD0355R	153	155	2	1.02	2.04
26IGRD0362	153	154	1	0.52	0.52
26IGRD0368	153	154	1	1.43	1.43
26IGRD0532	153	154	1	0.56	0.56
26IGRD0678	153	154	1	2.45	2.45
26IGRD0679	153	154	1	1.10	1.10
26IGRD0740	153	154	1	0.65	0.65
26IGRD0798	153	154	1	0.53	0.53
26IGRD0468	154	155	1	0.53	0.53
26IGRD0473	154	156	2	4.54	9.07
26IGRD0657	154	156	2	2.33	4.66
26IGRD0660	154	156	2	0.77	1.54
26IGRD0684	154	155	1	0.50	0.50
26IGRD0687	154	158	4	1.94	7.75



26IGRD0703	154	156	2	1.85	3.70
26IGRD0341	155	156	1	0.91	0.91
26IGRD0473A	155	156	1	1.37	1.37
26IGRD0677	155	164	9	1.26	11.33
26IGRD0717	155	156	1	0.56	0.56
26IGRD0760	155	156	1	1.18	1.18
26IGRD0762	155	156	1	0.69	0.69
26IGRD0800	155	156	1	0.50	0.50
26IGRD0362	156	163	7	1.37	9.58
26IGRD0461	156	159	3	0.61	1.82
26IGRD0487	156	160	4	1.56	6.22
26IGRD0693	156	157	1	0.79	0.79
26IGRD0702	156	157	1	0.70	0.70
26IGRD0463	157	158	1	0.80	0.80
26IGRD0625	157	158	1	0.50	0.50
26IGRD0645	157	158	1	7.06	7.06
26IGRD0656	157	160	3	11.30	33.91
26IGRD0678	157	158	1	1.43	1.43
26IGRD0684	157	169	12	3.07	36.86
26IGRD0685	157	181	24	2.54	60.93
26IGRD0686	157	160	3	2.06	6.18
26IGRD0705	157	165	8	2.33	18.60
26IGRD0800	157	158	1	0.98	0.98
26IGRD0611	158	166	8	18.03	144.24
26IGRD0614	158	159	1	1.00	1.00
26IGRD0693	158	160	2	3.42	6.83
26IGRD0762	158	159	1	0.58	0.58
26IGRD0404	159	160	1	3.02	3.02
26IGRD0473A	159	165	6	0.93	5.58
26IGRD0625	159	160	1	0.51	0.51
26IGRD0798	159	161	2	0.93	1.85
26IGRD0370	160	164	4	1.66	6.65
26IGRD0740	160	161	1	0.55	0.55
26IGRD0341	161	162	1	1.22	1.22
26IGRD0467	161	163	2	1.12	2.23
26IGRD0657	161	162	1	0.79	0.79
26IGRD0702	161	165	4	2.48	9.90
26IGRD0725	161	164	3	0.56	1.68
26IGRD0762	161	162	1	0.89	0.89
26IGRD0461	162	163	1	1.48	1.48
26IGRD0729	162	164	2	0.70	1.40
26IGRD0473	163	166	3	5.65	16.94
26IGRD0487	163	178	15	4.57	68.50
26IGRD0645	163	164	1	1.02	1.02



26IGRD0661	163	164	1	0.57	0.57
26IGRD0726	163	168	5	1.26	6.32
26IGRD0727	163	164	1	9.77	9.77
26IGRD0756	163	164	1	2.04	2.04
26IGRD0686	164	165	1	0.70	0.70
26IGRD0693	164	165	1	0.97	0.97
26IGRD0738	164	165	1	2.35	2.35
26IGRD0698	165	166	1	0.78	0.78
26IGRD0703	165	167	2	1.15	2.29
26IGRD0759	165	166	1	0.51	0.51
26IGRD0461	166	173	7	2.26	15.80
26IGRD0467	166	168	2	1.35	2.70
26IGRD0502	166	173	7	1.56	10.91
26IGRD0532	166	167	1	1.13	1.13
26IGRD0704	166	169	3	1.91	5.72
26IGRD0725	166	167	1	1.65	1.65
26IGRD0659	167	168	1	0.52	0.52
26IGRD0686	167	168	1	0.54	0.54
26IGRD0718	167	168	1	1.95	1.95
26IGRD0759	167	168	1	0.58	0.58
26IGRD0554	168	169	1	1.04	1.04
26IGRD0677	168	175	7	7.17	50.16
26IGRD0693	168	169	1	0.63	0.63
26IGRD0728	168	186	18	1.91	34.35
26IGRD0732	168	169	1	4.23	4.23
26IGRD0362	169	170	1	0.82	0.82
26IGRD0611	169	172	3	1.85	5.56
26IGRD0698	169	170	1	0.77	0.77
26IGRD0738	169	170	1	0.87	0.87
26IGRD0749	169	172	3	5.29	15.88
26IGRD0756	169	177	8	1.09	8.75
26IGRD0703	170	171	1	0.62	0.62
26IGRD0759	170	171	1	0.64	0.64
26IGRD0702	171	178	7	0.74	5.20
26IGRD0705	171	172	1	0.64	0.64
26IGRD0370	172	174	2	1.32	2.63
26IGRD0684	172	180	8	2.68	21.44
26IGRD0693	172	175	3	1.78	5.34
26IGRD0698	172	175	3	0.71	2.14
26IGRD0704	172	173	1	0.66	0.66
26IGRD0755	172	177	5	2.77	13.86
26IGRD0656	173	174	1	0.68	0.68
26IGRD0705	173	176	3	1.73	5.20
26IGRD0717	173	174	1	0.86	0.86



26IGRD0368	174	186	12	6.78	81.36
26IGRD0473A	174	175	1	3.20	3.20
26IGRD0609	174	175	1	0.93	0.93
26IGRD0656	175	176	1	0.77	0.77
26IGRD0484	176	177	1	2.10	2.10
26IGRD0758	176	177	1	0.61	0.61
26IGRD0370	177	180	3	1.07	3.21
26IGRD0609	177	178	1	0.52	0.52
26IGRD0686	177	179	2	0.67	1.34
26IGRD0704	177	178	1	0.88	0.88
26IGRD0717	177	180	3	3.96	11.89
26IGRD0760	177	178	1	2.26	2.26
26IGRD0698	178	179	1	0.55	0.55
26IGRD0341	179	180	1	0.54	0.54
26IGRD0362	179	180	1	0.62	0.62
26IGRD0461	179	180	1	0.83	0.83
26IGRD0613	179	180	1	0.60	0.60
26IGRD0659	179	181	2	0.69	1.37
26IGRD0693	179	191	12	3.23	38.77
26IGRD0609	180	182	2	1.26	2.52
26IGRD0718	180	188	8	0.79	6.30
26IGRD0341	181	182	1	0.68	0.68
26IGRD0473	181	182	1	1.71	1.71
26IGRD0703	181	186	5	3.47	17.33
26IGRD0463	182	185	3	0.62	1.86
26IGRD0487	182	185	3	1.65	4.95
26IGRD0502	182	204	22	1.69	37.27
26IGRD0532	182	183	1	1.26	1.26
26IGRD0705	182	183	1	0.51	0.51
26IGRD0799	182	183	1	1.06	1.06
26IGRD0362	183	184	1	0.83	0.83
26IGRD0684	183	185	2	2.46	4.91
26IGRD0717	183	184	1	86.80	86.80
26IGRD0742	183	185	2	1.25	2.49
26IGRD0677	184	186	2	1.05	2.10
26IGRD0678	184	185	1	0.55	0.55
26IGRD0418	185	186	1	4.35	4.35
26IGRD0473A	185	186	1	0.52	0.52
26IGRD0704	185	186	1	0.56	0.56
26IGRD0717	185	186	1	1.13	1.13
26IGRD0798	185	186	1	0.53	0.53
26IGRD0362	186	187	1	0.53	0.53
26IGRD0362	188	190	2	0.76	1.51
26IGRD0461	188	189	1	1.03	1.03



26IGRD0487	188	193	5	2.14	10.72
26IGRD0473A	189	194	5	1.10	5.52
26IGRD0685	189	192	3	1.53	4.59
26IGRD0704	189	190	1	0.66	0.66
26IGRD0611	190	192	2	2.34	4.67
26IGRD0684	190	191	1	0.98	0.98
26IGRD0702	190	198	8	3.54	28.30
26IGRD0727	191	192	1	0.66	0.66
26IGRD0554	192	193	1	1.35	1.35
26IGRD0341	193	199	6	4.88	29.26
26IGRD0461	193	196	3	6.76	20.29
26IGRD0362	194	195	1	0.52	0.52
26IGRD0659	195	196	1	0.82	0.82
26IGRD0362	196	200	4	0.55	2.21
26IGRD0473	196	198	2	0.94	1.88
26IGRD0487	196	197	1	0.67	0.67
26IGRD0684	196	199	3	1.18	3.53
26IGRD0685	196	197	1	0.73	0.73
26IGRD0717	196	204	8	3.42	27.37
26IGRD0698	197	198	1	0.79	0.79
26IGRD0718	197	199	2	0.78	1.56
26IGRD0727	197	200	3	0.86	2.58
26IGRD0473A	198	199	1	0.57	0.57
26IGRD0685	198	199	1	1.21	1.21
26IGRD0704	198	199	1	0.67	0.67
26IGRD0693	199	200	1	0.53	0.53
26IGRD0704	200	203	3	0.57	1.70
26IGRD0746	200	202	2	10.71	21.42
26IGRD0370	201	215	14	3.79	53.10
26IGRD0557	201	204	3	4.12	12.35
26IGRD0685	201	202	1	1.40	1.40
26IGRD0693	201	202	1	0.60	0.60
26IGRD0473	202	204	2	0.82	1.63
26IGRD0487	203	204	1	1.00	1.00
26IGRD0341	204	205	1	0.72	0.72
26IGRD0362	204	205	1	0.90	0.90
26IGRD0702	204	205	1	1.49	1.49
26IGRD0704	204	208	4	1.32	5.29
26IGRD0718	204	208	4	1.86	7.43
26IGRD0727	204	205	1	1.45	1.45
26IGRD0463	205	206	1	1.40	1.40
26IGRD0473A	206	207	1	0.58	0.58
26IGRD0487	207	208	1	0.87	0.87
26IGRD0502	207	210	3	0.68	2.03



26IGRD0684	207	208	1	1.24	1.24
26IGRD0717	207	209	2	0.76	1.51
26IGRD0341	208	209	1	0.56	0.56
26IGRD0473A	209	213	4	1.13	4.50
26IGRD0627	209	210	1	1.10	1.10
26IGRD0685	209	210	1	0.88	0.88
26IGRD0702	209	217	8	1.74	13.92
26IGRD0463	210	212	2	1.14	2.28
26IGRD0687	210	216	6	1.15	6.90
26IGRD0685	211	212	1	1.01	1.01
26IGRD0756	211	217	6	1.65	9.92
26IGRD0502	212	218	6	3.76	22.57
26IGRD0686	212	213	1	0.52	0.52
26IGRD0684	213	214	1	1.08	1.08
26IGRD0727	213	218	5	1.83	9.16
26IGRD0679	216	218	2	0.74	1.48
26IGRD0704	216	217	1	0.91	0.91
26IGRD0684	217	218	1	0.50	0.50
26IGRD0717	219	220	1	0.53	0.53
26IGRD0718	220	221	1	0.85	0.85
26IGRD0532	221	222	1	11.50	11.50
26IGRD0502	222	223	1	0.82	0.82
26IGRD0702	222	223	1	1.01	1.01
26IGRD0687	223	224	1	0.53	0.53
26IGRD0704	223	224	1	1.49	1.49
26IGRD0611	225	226	1	2.93	2.93
26IGRD0687	225	234	9	1.10	9.88
26IGRD0684	226	227	1	1.19	1.19
26IGRD0702	226	229	3	1.15	3.44
26IGRD0717	228	231	3	0.57	1.71
26IGRD0487	232	234	2	6.10	12.19
26IGRD0502	232	233	1	0.53	0.53
26IGRD0702	234	235	1	0.51	0.51
26IGRD0759	238	239	1	1.01	1.01
26IGRD0687	239	240	1	0.59	0.59
26IGRD0487	242	243	1	0.59	0.59
26IGRD0684	247	252	5	1.37	6.83
26IGRD0684	255	256	1	1.01	1.01

**Appendix 2: Collar Data for Drillholes Included in this ASX Release**

*All Holes located on Tenement M 16/262.*

*All Collar locations are from survey pickups, planned dip and azimuth is currently provided. All Collar Coordinates are provided as MGA95\_Zone 51.*

Hole No	Max Depth (m)	Grid	East	North	RL
26IGRD0341	222	MGA94_51	275491	6624180	523
26IGRD0355R	168	MGA94_51	275520	6624139	524
26IGRD0362	216	MGA94_51	275484	6624120	523
26IGRD0368	186	MGA94_51	275541	6624120	523
26IGRD0370	216	MGA94_51	275480	6624100	525
26IGRD0399	222	MGA94_51	275692	6623680	520
26IGRD0400	168	MGA94_51	275711	6623680	519
26IGRD0401	222	MGA94_51	275731	6623679	519
26IGRD0402	162	MGA94_51	275751	6623678	519
26IGRD0403	222	MGA94_51	275771	6623679	519
26IGRD0404	168	MGA94_51	275781	6623683	518
26IGRD0416	204	MGA94_51	275712	6623660	520
26IGRD0417	162	MGA94_51	275734	6623661	519
26IGRD0418	222	MGA94_51	275746	6623664	519
26IGRD0442	168	MGA94_51	275929	6623640	517
26IGRD0445	204	MGA94_51	275598	6623616	522
26IGRD0460	222	MGA94_51	276041	6623619	515
26IGRD0461	221	MGA94_51	275544	6623979	521
26IGRD0463	222	MGA94_51	275590	6623980	522
26IGRD0467	168	MGA94_51	275650	6623960	519
26IGRD0468	168	MGA94_51	275670	6623960	519
26IGRD0473	216	MGA94_51	275651	6623942	519
26IGRD0473A	222	MGA94_51	275653	6623940	515
26IGRD0484	216	MGA94_51	275820	6623900	514
26IGRD0487	258	MGA94_51	275602	6623876	518
26IGRD0495	18	MGA94_51	275774	6623880	518
26IGRD0496	222	MGA94_51	275810	6623880	515
26IGRD0497	138	MGA94_51	275830	6623880	514
26IGRD0502	258	MGA94_51	275602	6623861	518
26IGRD0532	222	MGA94_51	275680	6623740	519
26IGRD0542	138	MGA94_51	275700	6623720	519
26IGRD0554	222	MGA94_51	275680	6623699	520
26IGRD0557	222	MGA94_51	275741	6623699	519
26IGRD0600	222	MGA94_51	275871	6623760	516

26IGRD0601	138	MGA94_51	275891	6623759	516
26IGRD0602	138	MGA94_51	275911	6623760	515
26IGRD0602A	138	MGA94_51	275909	6623760	515
26IGRD0603	138	MGA94_51	275871	6623740	516
26IGRD0604	222	MGA94_51	275890	6623741	516
26IGRD0605	138	MGA94_51	275910	6623740	515
26IGRD0606	138	MGA94_51	275930	6623739	515
26IGRD0607	138	MGA94_51	275691	6623599	522
26IGRD0608	168	MGA94_51	275711	6623600	521
26IGRD0609	222	MGA94_51	275731	6623600	521
26IGRD0610	168	MGA94_51	275752	6623599	521
26IGRD0611	258	MGA94_51	275772	6623599	520
26IGRD0612	168	MGA94_51	275792	6623599	520
26IGRD0613	246	MGA94_51	275807	6623599	520
26IGRD0614	222	MGA94_51	275831	6623600	520
26IGRD0615	168	MGA94_51	275852	6623600	519
26IGRD0616	168	MGA94_51	275870	6623600	519
26IGRD0617	167	MGA94_51	275891	6623600	518
26IGRD0618	168	MGA94_51	275910	6623600	518
26IGRD0619	167	MGA94_51	275929	6623599	518
26IGRD0620	168	MGA94_51	275949	6623599	517
26IGRD0621	169	MGA94_51	275970	6623600	517
26IGRD0622	256	MGA94_51	275994	6623599	516
26IGRD0623	162	MGA94_51	276011	6623599	516
26IGRD0624	138	MGA94_51	275691	6623580	522
26IGRD0625	168	MGA94_51	275711	6623580	522
26IGRD0626	168	MGA94_51	275730	6623580	521
26IGRD0627	222	MGA94_51	275751	6623579	521
26IGRD0628	168	MGA94_51	275771	6623580	521
26IGRD0629	222	MGA94_51	275791	6623580	521
26IGRD0630	168	MGA94_51	275812	6623580	521
26IGRD0631	168	MGA94_51	275830	6623580	520
26IGRD0632	258	MGA94_51	275849	6623580	520
26IGRD0633	167	MGA94_51	275870	6623580	520
26IGRD0634	168	MGA94_51	275891	6623580	519
26IGRD0635	222	MGA94_51	275912	6623581	518
26IGRD0636	227	MGA94_51	275930	6623580	518
26IGRD0637	168	MGA94_51	275951	6623580	518
26IGRD0638	168	MGA94_51	275970	6623579	517
26IGRD0639	168	MGA94_51	275989	6623578	516
26IGRD0640	138	MGA94_51	275690	6623558	523
26IGRD0641	138	MGA94_51	275709	6623559	522
26IGRD0642	222	MGA94_51	275730	6623560	522
26IGRD0643	168	MGA94_51	275750	6623560	522

26IGRD0644	258	MGA94_51	275772	6623560	521
26IGRD0645	168	MGA94_51	275792	6623560	521
26IGRD0646	168	MGA94_51	275811	6623560	521
26IGRD0647	192	MGA94_51	275832	6623561	521
26IGRD0648	168	MGA94_51	275851	6623560	520
26IGRD0649	168	MGA94_51	275869	6623560	520
26IGRD0650	168	MGA94_51	275889	6623560	520
26IGRD0651	168	MGA94_51	275910	6623560	519
26IGRD0652	168	MGA94_51	275930	6623560	519
26IGRD0653	168	MGA94_51	275949	6623560	518
26IGRD0654	215	MGA94_51	275970	6623560	517
26IGRD0655	168	MGA94_51	275991	6623561	517
26IGRD0656	210	MGA94_51	275691	6623540	522
26IGRD0657	168	MGA94_51	275711	6623541	522
26IGRD0658	168	MGA94_51	275731	6623541	522
26IGRD0659	222	MGA94_51	275752	6623540	522
26IGRD0660	167	MGA94_51	275769	6623540	522
26IGRD0661	168	MGA94_51	275790	6623540	521
26IGRD0662	168	MGA94_51	275811	6623540	521
26IGRD0663	168	MGA94_51	275830	6623540	521
26IGRD0664	222	MGA94_51	275851	6623540	521
26IGRD0665	168	MGA94_51	275870	6623540	520
26IGRD0666	258	MGA94_51	275890	6623539	520
26IGRD0667	168	MGA94_51	275911	6623540	519
26IGRD0668	168	MGA94_51	275931	6623540	519
26IGRD0669	168	MGA94_51	275950	6623540	518
26IGRD0670	168	MGA94_51	275970	6623540	518
26IGRD0671	168	MGA94_51	275989	6623541	517
26IGRD0677	222	MGA94_51	275721	6623879	519
26IGRD0678	221	MGA94_51	275741	6623880	519
26IGRD0679	221	MGA94_51	275761	6623880	518
26IGRD0680	258	MGA94_51	275781	6623879	517
26IGRD0680B	198	MGA94_51	275780	6623890	517
26IGRD0681	222	MGA94_51	275796	6623879	516
26IGRD0682	221	MGA94_51	275808	6623878	515
26IGRD0684	258	MGA94_51	275629	6623858	518
26IGRD0685	222	MGA94_51	275650	6623858	518
26IGRD0686	222	MGA94_51	275670	6623860	520
26IGRD0687	258	MGA94_51	275690	6623860	520
26IGRD0693	221	MGA94_51	275662	6623840	520
26IGRD0698	238	MGA94_51	275760	6623840	518
26IGRD0700	168	MGA94_51	275811	6623838	515
26IGRD0701	168	MGA94_51	275830	6623840	514
26IGRD0702	258	MGA94_51	275630	6623820	520

26IGRD0703	186	MGA94_51	275640	6623820	520
26IGRD0704	258	MGA94_51	275650	6623820	520
26IGRD0705	186	MGA94_51	275660	6623820	520
26IGRD0710	186	MGA94_51	275781	6623820	518
26IGRD0711	186	MGA94_51	275801	6623819	517
26IGRD0712	222	MGA94_51	275823	6623819	515
26IGRD0713	186	MGA94_51	275841	6623819	514
26IGRD0714	186	MGA94_51	275862	6623820	513
26IGRD0717	258	MGA94_51	275653	6623800	520
26IGRD0718	222	MGA94_51	275672	6623799	519
26IGRD0725	168	MGA94_51	275653	6623780	520
26IGRD0726	186	MGA94_51	275671	6623781	519
26IGRD0727	222	MGA94_51	275691	6623781	518
26IGRD0728	186	MGA94_51	275710	6623781	518
26IGRD0729	258	MGA94_51	275731	6623781	517
26IGRD0731	168	MGA94_51	275770	6623780	516
26IGRD0732	222	MGA94_51	275791	6623780	516
26IGRD0733	258	MGA94_51	275700	6623960	517
26IGRD0735	138	MGA94_51	275720	6623960	516
26IGRD0737	138	MGA94_51	275740	6623960	516
26IGRD0738	258	MGA94_51	275680	6623940	518
26IGRD0740	186	MGA94_51	275700	6623940	519
26IGRD0742	222	MGA94_51	275720	6623940	518
26IGRD0744	186	MGA94_51	275740	6623940	518
26IGRD0746	258	MGA94_51	275760	6623940	516
26IGRD0749	186	MGA94_51	275720	6623920	519
26IGRD0751	186	MGA94_51	275740	6623920	518
26IGRD0753	186	MGA94_51	275760	6623920	518
26IGRD0755	186	MGA94_51	275780	6623920	516
26IGRD0756	222	MGA94_51	275700	6623900	520
26IGRD0758	186	MGA94_51	275722	6623899	519
26IGRD0759	258	MGA94_51	275732	6623900	519
26IGRD0760	186	MGA94_51	275742	6623900	519
26IGRD0761	186	MGA94_51	275751	6623900	519
26IGRD0762	186	MGA94_51	275761	6623900	518
26IGRD0763	186	MGA94_51	275772	6623899	517
26IGRD0764	244	MGA94_51	275782	6623899	516
26IGRD0765	186	MGA94_51	275793	6623898	515
26IGRD0766	186	MGA94_51	275801	6623898	515
26IGRD0781	168	MGA94_51	275902	6623640	517
26IGRD0782	168	MGA94_51	275920	6623640	517
26IGRD0793	84	MGA94_51	275680	6623980	517
26IGRD0794	90	MGA94_51	275700	6623980	516
26IGRD0795	118	MGA94_51	275720	6623980	516

26IGRD0796	118	MGA94_51	275725	6623980	516
26IGRD0797	150	MGA94_51	275770	6623980	514
26IGRD0798	186	MGA94_51	275790	6623980	514
26IGRD0799	186	MGA94_51	275810	6623980	515
26IGRD0800	222	MGA94_51	275830	6623980	514
26IGRD0801	138	MGA94_51	275849	6623981	514
26IGRD0802	138	MGA94_51	275869	6623980	514
26IGRD0803	138	MGA94_51	275890	6623980	513
26IGRD0804	102	MGA94_51	275849	6623961	515
26IGRD0805	120	MGA94_51	275870	6623960	514
26IGRD0806	144	MGA94_51	275889	6623960	514
26IGRD0809	102	MGA94_51	275869	6623940	514
26IGRD0810	120	MGA94_51	275890	6623939	514
26IGRD0814	84	MGA94_51	275869	6623921	514
26IGRD0815	74	MGA94_51	275890	6623920	514
26IGRD0818	156	MGA94_51	275950	6623920	513
26IGRD0819	156	MGA94_51	275970	6623920	512
26IGRD0822	144	MGA94_51	275960	6623900	511
26IGRD0823	144	MGA94_51	275980	6623900	511
26IGRD0824	72	MGA94_51	275929	6623879	512
26IGRD0825	90	MGA94_51	275949	6623880	512
26IGRD0826	102	MGA94_51	275970	6623880	511
26IGRD0827	126	MGA94_51	275990	6623880	511
26IGRD0828	84	MGA94_51	275929	6623860	512
26IGRD0829	102	MGA94_51	275949	6623860	512
26IGRD0830	120	MGA94_51	275969	6623860	512
26IGRD0831	132	MGA94_51	275988	6623860	511
26IGRD0832	84	MGA94_51	275932	6623841	512
26IGRD0835	108	MGA94_51	275989	6623820	512

## Appendix 3: JORC Tables.

### Section 1: Sampling Techniques and Data

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
<b>Sampling techniques</b>	<p><i>Nature and quality of sampling (e.g. cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc.). These examples should not be taken as limiting the broad meaning of sampling.</i></p> <p><i>Include reference to measures taken to ensure sample representativity and the appropriate calibration of any measurement tools or systems used.</i></p> <p><i>Aspects of the determination of mineralisation that are Material to the Public Report. In cases where 'industry standard' work has been done this would be relatively simple (e.g. 'reverse circulation drilling was used to obtain 1 m samples from which 3 kg was pulverised to produce a 30 g charge for fire assay'). In other cases more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or mineralisation types (e.g. submarine nodules) may warrant disclosure of detailed information.</i></p>	<p>Aberfoyle:</p> <ul style="list-style-type: none"> <li>Reverse circulation (RC), rotary air blast (RAB) and aircore (AC) drilling with 1 m sampling from cyclone (BDRB prefix holes RAB drilling with 2 m sampling). Samples sent to accredited laboratories for drying, crushing and pulverising. Composite samples assayed by aqua regia/atomic absorption spectroscopy (AAS) (except in areas of elevated graphite – fire assay (FA) and those returning greater than 0.2–0.3 g/t were re-assayed as individual metres by FA to ALS Kalgoorlie for 50 g charge FA with 0.01 ppm detection limit. HQ triple diamond (DD) drilling was halved, 50 g charge FA with 0.01 ppm detection limit.</li> </ul> <p>EGL:</p> <ul style="list-style-type: none"> <li>RC samples collected from the riffle or cone splitter directly off rig into calico bags. Splitter maintained on level site to ensure sample representativity. 1 m samples are dried, crushed, pulverised and a 40 g charge is analysed by FA.</li> </ul> <p>Roper River Resources:</p> <ul style="list-style-type: none"> <li>RAB 1 m sampling with blade or hammer. Dried, crushed and pulverised samples analysed by aqua regia/AAS finish with 25 g charge.</li> </ul> <p>Monarch:</p> <ul style="list-style-type: none"> <li>AC, RAB and RC drilling on 1 m sampling basis with RAB samples being composited to 4 m for initial analysis by aqua regia/AAS. Individual AC and RC metres collected from cyclone, riffle split and submitted for aqua regia/AAS and FA/AAS respectively.</li> </ul> <p>Siberia Mining Corporation (SMC):</p> <ul style="list-style-type: none"> <li>1 m sampling of AC, RAB and RC drilling composites and individual re-assays dispatched for FA.</li> </ul> <p>Perilya:</p> <ul style="list-style-type: none"> <li>5 m composite RAB and AC assayed at Analabs Perth by method P649, 50 g aqua regia, DIBK, Carbon Rod.</li> </ul> <p>Croesus:</p>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<ul style="list-style-type: none"> <li>RC 1 m samples collected under cyclone. RAB drilling on a 1 m basis. 3.5 kg samples were pulverised to make 50 g charge for analysis by FA/inductively coupled plasma-optical spectrometry (ICP-OS).</li> </ul> <p>Delta:</p> <ul style="list-style-type: none"> <li>1 m sampling of AC, RAB and RC. 5 m composites submitted to Genalysis and/or ALS laboratories Kalgoorlie for preparation, followed by aqua regia with 50 g charge with 0.01 ppm detection limit. Composite assays returning values <math>\geq 0.1</math> ppm Au, corresponding single metre samples were collected and submitted.</li> </ul> <p>Ora Banda Mining Ltd (OBM):</p> <ul style="list-style-type: none"> <li>1 m RC samples using face sampling hammer with samples collected under cone splitter.</li> <li>4 m composite RC samples collected using a PVC spear from the sample piles at the drill site. For drilling up to April 2020, RC samples were submitted for pulverising and 50 g charge FA. 4 m composite samples with gold values greater than 0.2 g/t Au were re-sampled as 1 m split samples and submitted to the lab for further analysis. Half-core samples, cut by automated core saw. Core sample intervals selected by geologist and defined by geological boundaries. Samples are crushed, pulverised and a 40 g charge is analysed by FA.</li> <li>A total of 56 holes were drilled by OBM, including three RCDD holes and 53 RC holes.</li> </ul> <p>The information presented above is derived from OBM's JORC table for its 2022 Iguana MRE.</p> <p>Beacon Minerals</p> <ul style="list-style-type: none"> <li>1m RC samples using face hammer with samples collected under cone splitter.</li> <li>4m composite AC samples collected via scoop on sample piles. 4 m composite samples with gold values greater than 0.2 g/t Au were re-sampled as 1 m split samples and submitted to the lab for further analysis.</li> <li>DD logged and full hole sampled utilising geology defined sample intervals. Core was halved or quartered depending on use and dispatched to the BV Cunningham facility.</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<ul style="list-style-type: none"> <li>All Assays conducted for Beacon Minerals were performed by BV Cunninham. Samples are crushed, pulverised and a 40 g charge is analysed by FA.</li> </ul>
<b>Drilling techniques</b>	<p><i>Drill type (e.g. core, reverse circulation, open-hole hammer, rotary air blast, auger, Bangka, sonic, etc) and details (e.g. core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc).</i></p>	<p>Aberfoyle:</p> <ul style="list-style-type: none"> <li>No details for early RAB drilling. Later drilling involved RAB drilling using 4–4.25-inch blade or hammer to blade refusal.</li> <li>AC using 3.5-inch blade.</li> <li>RC 5.25–5.5-inch diameter face sampling hammer.</li> </ul> <p>Croesus:</p> <ul style="list-style-type: none"> <li>Undocumented details. Presumably industry standard at the time being 5.5-inch face sampling hammers for RC and 4-inch diameter RAB holes.</li> </ul> <p>Delta:</p> <ul style="list-style-type: none"> <li>RC 5.5-inch face sampling hammers. At times, a stepped AC bit was used to drill through sand at beginning of hole which changed to face-sampling hammer when laterite encountered.</li> <li>HQ triple twin DD holes at Lizard. LZD1-3 was oriented.</li> </ul> <p>EGL:</p> <ul style="list-style-type: none"> <li>RC 5.25-inch diameter.</li> </ul> <p>Roper River Resources:</p> <ul style="list-style-type: none"> <li>RAB with blade and/or hammer bit.</li> <li>RC drilling with 5.25-inch diameter face sampling hammer.</li> </ul> <p>Monarch:</p> <ul style="list-style-type: none"> <li>RC drilling 5.5-inch diameter with face sampling hammer.</li> <li>RAB 4-inch diameter blade with occasional hammer bit usage.</li> <li>AC details undocumented.</li> </ul> <p>SMC:</p> <ul style="list-style-type: none"> <li>AC, RAB, RC details undocumented. Presumably industry standard at the time being 5.5-inch face sampling hammers for RC and 4-inch diameter RAB holes.</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<p>OBM:</p> <ul style="list-style-type: none"> <li>• 5.25–5.5-inch diameter RC holes using face sampling hammer with samples collected under cone splitter. HQ and HQ3 coring to approx. 40 m, then NQ2 to bottom of hole.</li> <li>• Metallurgical and geotechnical core holes drilled using HQ3 exclusively.</li> <li>• All core oriented by reflex instrument.</li> </ul> <p>The information presented above is derived from OBM's JORC table for its 2022 Iguana MRE.</p> <p>Beacon Minerals:</p> <ul style="list-style-type: none"> <li>• RC drilling conducted by 115mm Hammer face bit.</li> <li>• AC drilling conducted utilising both Blade and Hammer methods, varying in bit size due to ground conditions</li> <li>• DD drilling was conducted in PQ3 or HQ3. Two holes were collared in PQ3 before casing off at approx. 70m depth to HQ3. Remaining holes were drilled HQ3 from collar.</li> </ul>
<p><b>Drill sample recovery</b></p>	<p><i>Method of recording and assessing core and chip sample recoveries and results assessed.</i></p> <p><i>Measures taken to maximise sample recovery and ensure representative nature of the samples.</i></p> <p><i>Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.</i></p>	<p>Delta:</p> <ul style="list-style-type: none"> <li>• Recoveries for resource RC drilling made as a subjective estimate. Recoveries in resource drilling were generally in excess of 70% (Iguana laterite), 60% (Lizard). Poor recoveries occurred outside mineralised zones.</li> </ul> <p>OBM:</p> <ul style="list-style-type: none"> <li>• DD drill recoveries are recorded as a percentage calculated from measured core against downhole drilled intervals (core blocks).</li> <li>• RC samples are weighed at the laboratory to monitor recoveries.</li> </ul> <p>Other operators have not captured recovery data.</p> <p>There is no known relationship between sample recovery and grade.</p> <p>The information presented above is derived from OBM's JORC table for its 2022 Iguana MRE.</p> <p>Beacon Minerals:</p> <ul style="list-style-type: none"> <li>• DD drill recoveries were recorded in logging and sampling processes, with noted core loss existing in upper weathering profiles</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<ul style="list-style-type: none"> <li>RC sample had recoveries recorded by percentage of material, significant material loss was present near surface due to unconsolidated sands</li> <li>AC sample had recoveries recorded in percentage, material retention was good to excellent from surface.</li> </ul>
<p><b>Logging</b></p>	<p><i>Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies.</i></p> <p><i>Whether logging is qualitative or quantitative in nature. Core (or costean, channel, etc.) photography.</i></p> <p><i>The total length and percentage of the relevant intersections logged.</i></p>	<p>Aberfoyle:</p> <ul style="list-style-type: none"> <li>Logging on 1 m basis.</li> <li>Qualitative – lithology, oxidation, grain size.</li> <li>Quantitative – quartz.</li> </ul> <p>Croesus:</p> <ul style="list-style-type: none"> <li>Qualitative – lithology, colour, grain size, alteration, oxidation, texture, structures, regolith.</li> <li>Quantitative – estimates are made of quartz veining.</li> </ul> <p>Delta:</p> <ul style="list-style-type: none"> <li>Qualitative – lithology, colour, oxidation, structure, texture, alteration.</li> <li>Quantitative – estimates are made of quartz veining and minerals.</li> </ul> <p>EGL:</p> <ul style="list-style-type: none"> <li>Qualitative – alteration, colour, grain size, lithology, oxidation, mineralogy, structure, texture, vein style, vein assemblage, remarks.</li> <li>Quantitative – mineralisation intensity, vein percent.</li> </ul> <p>Roper River Resources:</p> <ul style="list-style-type: none"> <li>Qualitative – colour, lithology, oxidation, BOCO, texture, alteration, minerals, sulphides.</li> <li>Quantitative – quartz.</li> </ul> <p>Monarch:</p> <ul style="list-style-type: none"> <li>Qualitative – lithology, colour, oxidation, grain size, texture, structure, hardness, regolith.</li> <li>Quantitative – estimates are made of quartz veining, sulphide percentages.</li> </ul> <p>SMC:</p> <ul style="list-style-type: none"> <li>Qualitative – lithology, colour, oxidation, alteration.</li> <li>Quantitative – estimates are made of quartz veining.</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<p>OBM:</p> <ul style="list-style-type: none"> <li>Field logging was conducted using Geobank Mobile™ software on Panasonic Toughbook CF-31 ruggedised laptop computers.</li> <li>Qualitative logging – lithology, colour, oxidation, grain size, texture, structure, hardness, regolith.</li> <li>Quantitative – estimates are made of quartz veining, sulphide and alteration percentages. Core photographed both wet and dry.</li> <li>Magnetic susceptibility and rock quality designation (RQD) were also recorded for core holes.</li> </ul> <p>All holes were geologically logged in their entirety to a level of detail to support Mineral Resource estimation.</p> <p>The information presented above is derived from OBM’s JORC table for its 2022 Iguana MRE.</p> <p>Beacon Minerals:</p> <ul style="list-style-type: none"> <li>Diamond Drilling- Logging was completed by competent contractors utilising Beacon logging template. Sampling was then conducted off the logging intervals.</li> <li>Reverse Circulation/ Air Core- Logging was conducted using chip samples, prepared by conducting both dry and wet sieves. Logging was done in accordance with the Beacon Logging code.</li> </ul>
<p><b>Subsampling techniques and sample preparation</b></p>	<p><i>If core, whether cut or sawn and whether quarter, half or all core taken.</i></p> <p><i>If non-core, whether riffled, tube sampled, rotary split, etc and whether sampled wet or dry.</i></p> <p><i>For all sample types, the nature, quality and appropriateness of the sample preparation technique.</i></p> <p><i>Quality control procedures adopted for all subsampling stages to maximise representativity of samples.</i></p> <p><i>Measures taken to ensure that the sampling is representative of the in-situ material collected, including for instance results for field duplicate/second-half sampling.</i></p>	<p>Aberfoyle:</p> <ul style="list-style-type: none"> <li>Early (~1990) drilling – 2 m samples composited to 6m by undocumented method. Results returning &gt;0.2 g/t re-sampled on a 2 m basis.</li> <li>Subsequent drilling – RAB/AC 2 m surface composites and 4 m composite thereafter. RC 1 m samples riffle split and composited to 4 m samples. Composite assays returning greater than 0.2 g/t re-sampled on a metre basis.</li> </ul> <p>Croesus:</p> <ul style="list-style-type: none"> <li>RAB drill samples were collected in buckets below a freestanding cyclone and laid out at 1 m intervals in rows of ten metres adjacent to the drill collar.</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
	<p><i>Whether sample sizes are appropriate to the grain size of the material being sampled.</i></p>	<ul style="list-style-type: none"> <li>• Composite analytical samples (~3.5 kg) were initially collected over 5 m intervals for each hole and a 1 m bottom of hole analytical sample. Analytical composite samples were collected by taking a representative scoop through each 1 m drill sample. Composite assays returning greater than 100 ppb Au were resampled on an individual basis by an undocumented method.</li> <li>• RC drill samples were riffle split at 1 m intervals off the rig into calico bags whilst excess material was placed on the ground in 1 m piles for logging. The analytical samples were dried, crushed and split to obtain a sample less than 3.5 kg, and then fine pulverised prior to a 50 g sample being taken for analysis.</li> </ul> <p>Delta:</p> <ul style="list-style-type: none"> <li>• RC: Samples collected on 1 m intervals via a cyclone into green plastic bags. Each bag was riffle split if dry to a 2–3 kg sample and retained on site. A PVC spear sample was taken from residues to create a 5 m composite. If composites returned values <math>\geq 0.1</math> g/t, geologically interesting or had elevated arsenic levels, the original 1 m splits were collected and submitted. Original wet samples were split at this stage using wet triple riffle splitter, washed between samples. Wet samples were rare and usually outside of main mineralisation.</li> <li>• RAB: Typically 1 m samples were composited to 5 m (occasionally 10 m) by PVC spear. Significant assay results were re-submitted on a single metre basis.</li> <li>• DD: Core was halved. Sample length typically 1 m.</li> </ul> <p>EGL:</p> <ul style="list-style-type: none"> <li>• RC samples riffle split into calico bags. Wet or moist samples are noted during sampling. Core was cut with diamond saw and half core sampled. All mineralised zones are sampled, including portions of visibly unmineralised hangingwall and footwall zones. Sample weights range from &gt;1.0 kg to 3.5 kg. Samples weighed by laboratory, dried and split to &lt;3 kg if necessary and pulverised by LM-5. Field duplicates, blanks and standards were submitted for QAQC analysis.</li> </ul> <p>Roper River Resources:</p> <ul style="list-style-type: none"> <li>• RAB and RC holes were composited to 6 m and 4 m respectively with anomalous zones of nickel or gold being resubmitted on a metre basis.</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<p>Monarch:</p> <ul style="list-style-type: none"> <li>• RAB: 2 – 4 m composites scoop sampled.</li> <li>• AC and RC 1 m splits via riffle splitter.</li> <li>• RAB samples were composited to 4 m by scoop for initial analysis. Samples were riffle split and prepared with single stage mix and grinding.</li> </ul> <p>SMC:</p> <ul style="list-style-type: none"> <li>• RAB samples were collected at 1 m intervals from the drillhole collar using a plastic bucket and laid on the ground. A scoop sample was taken from each sample to form 4 m or 5 m composite.</li> <li>• AC: Predominantly 4 m composite samples. Methods unknown.</li> <li>• RAB samples were collected at 1 m intervals from the drillhole collar using a plastic bucket and laid on the ground. A scoop sample was taken from each sample to form a 5 m composite.</li> <li>• AC: Predominantly 4 m composite samples.</li> <li>• RAB: Predominantly 5 m composite samples.</li> </ul> <p>OBM:</p> <ul style="list-style-type: none"> <li>• RC samples were submitted either as individual 1 m samples taken onsite from cone splitter or as 4 m composite samples speared from the onsite drill sample piles. Half-core samples, cut by saw. Core sample intervals selected by geologist and defined by geological boundaries.</li> <li>• For drilling up to April 2020, RC samples were dried, crushed, split, pulverised and a 50 g charge taken. 4 m composite samples with gold values greater than 0.2 g/t Au were re-sampled as 1 m split samples and submitted to the lab for further analysis.</li> <li>• Field duplicates, blanks and standards were submitted for quality assurance and quality control (QAQC) analysis. Repeat assays were undertaken on pulp samples at the discretion of the laboratory.</li> </ul> <p>The information presented above is derived from OBM’s JORC table for its 2022 Iguana MRE.</p> <p>Beacon Minerals:</p>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<ul style="list-style-type: none"> <li>RC/AC samples were submitted either as individual 1 m samples taken onsite from cone splitter or as 4 m composite samples scooped from the onsite drill sample piles. Any 4m composites which exceeded 0.3g/t or where otherwise noted as anomalous were selected for re-sample and had 1m sample bags dispatched to the lab with these results over-writing the prior composite results</li> <li>DD drill were half-core samples, cut by saw. Core sample intervals selected by geologist and defined by geological boundaries.</li> </ul> <p>Field duplicates, blanks and standards were submitted for quality assurance and quality control (QAQC) analysis. Repeat assays were undertaken on pulp samples at the discretion of the laboratory.</p>
<b>Quality of assay data and laboratory tests</b>	<p><i>The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total.</i></p> <p><i>For geophysical tools, spectrometers, handheld XRF instruments, etc, the parameters used in determining the analysis including instrument make and model, reading times, calibrations factors applied and their derivation, etc.</i></p> <p><i>Nature of quality control procedures adopted (e.g. standards, blanks, duplicates, external laboratory checks) and whether acceptable levels of accuracy (i.e. lack of bias) and precision have been established.</i></p>	<p>Aberfoyle:</p> <ul style="list-style-type: none"> <li>RC/RAB: composites assayed by aqua regia AAS. Composites returning &gt;0.2–0.3g/t Au re-submitted as 1 m samples by 50 g charge FA.</li> <li>AC: Composites by 50 g charge FA. Composites returning &gt;0.2–0.3g/t Au re-submitted as 1 m samples for FA again.</li> <li>In areas of elevated graphite (Burke Dam), RC composites were assayed by 50 g FA. Assayed at Genalysis.</li> </ul> <p>Croesus:</p> <ul style="list-style-type: none"> <li>50 g charge analysed for gold (FA/ICP-Os) by Analabs Kalgoorlie for RC and Ultratrace Perth for RAB. Lab repeats at discretion of laboratory.</li> </ul> <p>Delta:</p> <ul style="list-style-type: none"> <li>RC and RAB: 5 m composites dispatched to Genalysis and/or ALS laboratories Kalgoorlie for aqua regia with 50 g charge with 0.01 ppm detection limit. Composite assays returning values <math>\geq 0.1</math> ppm Au, corresponding single metre samples were collected and despatched to ALS Kalgoorlie for 50 g charge FA with 0.01 ppm detection limit. Core despatched to Genalysis Kalgoorlie for 50 g charge FA with 0.01ppm detection limit. Standards of an undocumented provenance and locally (uncertified) sourced blanks inserted but frequency undocumented. One in 20 pulp duplicate frequency. Blind pulp re-assays performed.</li> </ul> <p>EGL:</p>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<ul style="list-style-type: none"> <li>• Samples were sent to Kalgoorlie Assay Laboratories to be analysed for gold by 40 g FA. Samples were also analysed at Genalysis. Certified reference material (CRM) standards were submitted. Field duplicate samples taken at rate of 1:40.</li> </ul> <p>Roper River Resources:</p> <ul style="list-style-type: none"> <li>• 25 g sample by aqua regia/AAS finish at MiniLab Kalgoorlie. Lab repeats at discretion of laboratory.</li> </ul> <p>Monarch:</p> <ul style="list-style-type: none"> <li>• RAB and AC: Assayed by aqua regia/AAS with 10 ppb detection limit.</li> <li>• RC: 50 g charge FA/AAS at SGS Kalgoorlie.</li> </ul> <p>SMC:</p> <ul style="list-style-type: none"> <li>• FA, undocumented charge and laboratory.</li> </ul> <p>OBM:</p> <ul style="list-style-type: none"> <li>• Up to April 2020, all samples were sent to an accredited laboratory (Nagrom Laboratories in Perth, Intertek-Genalysis in Kalgoorlie or SGS in Kalgoorlie). The samples have been analysed by firing a 50 g portion of the sample. This is the classical fire assay process and will give total separation of gold. An ICP-OES finish is used. Commercially prepared standard samples and blanks are inserted in the sample stream at a rate of 1:12. Sizing results (percentage of pulverised sample passing a 75 µm mesh) are undertaken on approximately 1 in 40 samples. The accuracy (standards) and precision (repeats) of assaying are acceptable. Standards and blanks were inserted into the sample stream at a rate of approximately 1:12. Duplicates were submitted at a rate of approximately 1:30.</li> <li>• Fire assay is considered a total technique, aqua regia is considered partial.</li> </ul> <p>Beacon Minerals:</p> <ul style="list-style-type: none"> <li>• All assay work was conducted by BV Cunningham utilising FA/AAS analysis with 40g charge. Beacon Minerals submitted QA/QC samples every 20 samples utilising multiple different CRM providers.</li> </ul>
<b>Verification of sampling and assaying</b>	<p><i>The verification of significant intersections by either independent or alternative company personnel.</i></p> <p><i>The use of twinned holes.</i></p>	<p>Holes are not deliberately twinned in Iguana area.</p> <p>Monarch:</p>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
	<p><i>Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols.</i></p> <p><i>Discuss any adjustment to assay data.</i></p>	<ul style="list-style-type: none"> <li>Geological and sample data was logged digitally and .csv or .xls files imported into Datashed SQL database with in-built validation. Samples bags were placed into numbered plastic bags and then cable tied. Samples collected daily from site by laboratory.</li> </ul> <p>EGL:</p> <ul style="list-style-type: none"> <li>Geological and sample data logged directly into field computer at the core yard using Field Marshall. Data is transferred to Perth via email and imported into Geobank SQL database by the database administrator (DBA). Assay files are received in .csv format and loaded directly into the database by the DBA. Hardcopy and/or digital copies of data are kept for reference if necessary.</li> </ul> <p>OBM:</p> <ul style="list-style-type: none"> <li>Geological and sample data logged directly into field computer at the drill rig or core yard using Field Marshall or Geobank Mobile. Data is transferred to Perth via email and imported into Geobank SQL database by the DBA. Assay files are received in .csv format and loaded directly into the database by the DBA. Hardcopy and/or digital copies of data are kept for reference if necessary.</li> </ul> <p>Data entry, verification and storage protocols for remaining operators is unknown.</p> <p>The information presented above is derived from OBM's JORC table for its 2022 Iguana MRE.</p> <p>Beacon Minerals:</p> <ul style="list-style-type: none"> <li>Geological and sampling data was entered directly into a formatted excel file in the field which was then verified. Data was then formatted and imported into a secured on-site database by a suitably qualified database geologist</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
<b>Location of data points</b>	<p><i>Accuracy and quality of surveys used to locate drillholes (collar and downhole surveys), trenches, mine workings and other locations used in Mineral Resource estimation.</i></p> <p><i>Specification of the grid system used.</i></p> <p><i>Quality and adequacy of topographic control.</i></p>	<p>Aberfoyle:</p> <ul style="list-style-type: none"> <li>All drilling not surveyed. Collars located on AMG Zone 51 Grid utilised.</li> </ul> <p>Croesus:</p> <ul style="list-style-type: none"> <li>TGRC holes were collar surveyed in AMG Zone 51 Grid. No downhole surveys.</li> </ul> <p>Delta:</p> <ul style="list-style-type: none"> <li>All drillholes used for resource definition surveyed by Minecomp. All post-1993 RC and DD holes downhole surveyed using EMS or Eastman single shot where possible. Where not possible, data from proximal holes was used. LAD and LZC, LZD, LAC, and selected G prefixed holes downhole surveyed by undocumented method approximately every 10 m. Many RAB holes appear to be collar surveyed.</li> <li>AMG Zone 51 Grid utilised except for holes in the Nyborgs region where a local grid (Lady Ida) was utilised.</li> </ul> <p>EGL:</p> <ul style="list-style-type: none"> <li>Collars were surveyed by differential global positioning system (GPS) in MGA Zone 51. No downhole surveying performed.</li> </ul> <p>Roper River Resources:</p> <ul style="list-style-type: none"> <li>No surveys post drilling. AMG Zone 51 Grid utilised.</li> </ul> <p>Monarch:</p> <ul style="list-style-type: none"> <li>RC and some AC collars surveyed by differential GPS. All remaining holes surveyed by GPS. MGA Zone 51 Grid utilised. IGRC holes were downhole surveyed by EMS every 5 m. RC drilling was surveyed by Electronic Multi-shot on selected holes.</li> </ul> <p>SMC:</p> <ul style="list-style-type: none"> <li>No evidence of post drilling surveys, MGA Zone 51 Grid utilised.</li> </ul> <p>OBM:</p> <ul style="list-style-type: none"> <li>(RC, DD) MGA94, Zone 51. Drillhole collar positions were picked up by a contract surveyor using RTK GPS subsequent to drilling.</li> <li>Drillhole, downhole surveys are recorded every 30 m using a reflex digital downhole camera. Some RC holes not surveyed if holes short and/or drilling an early-stage exploration project. DD drillholes completed in 2019 and 2020 by OBM were surveyed using a Gyro tool.</li> </ul>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<p>The information presented above is derived from OBM's JORC table for its 2022 Iguana MRE.</p> <p>Beacon Minerals:</p> <ul style="list-style-type: none"> <li>• Collars were picked up by a qualified surveyor in MGA94 Z 51 format utilising a RTK GPS and appropriately set control. Locations were also cross checked with hand held GPS.</li> <li>• DD Holes were surveyed using a Reflex Continuous Gyro system.</li> <li>• RC Holes were surveyed at EOH depth only, with a partial portion of the program surveyed 6m (1 rod) from EOH to avoid loss of instrument or hole collapse.</li> </ul>
<b>Data spacing and distribution</b>	<p><i>Data spacing for reporting of Exploration Results.</i></p> <p><i>Whether the data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied.</i></p> <p><i>Whether sample compositing has been applied.</i></p>	<ul style="list-style-type: none"> <li>• Exploration results are reported for single holes only.</li> <li>• Data spacing highly variable from wide spaced ~800 m x ~80 m regional RAB to close spaced resource drilling ~10 m x ~10 m and grade control drilling at ~5 m x ~5 m.</li> <li>• Drillhole spacing is adequate to establish geological and grade continuity for the Iguana deposit.</li> <li>• Drill composites have been length weighted, 0.5 g/t lower cut-off, not top cut, maximum 3 m internal dilution.</li> </ul>
<b>Orientation of data in relation to geological structure</b>	<p><i>Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type.</i></p> <p><i>If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material.</i></p>	<ul style="list-style-type: none"> <li>• Deposits in the Lady Ida area are generally oriented on northwest trends. Once the orientation of mineralisation was established, drilling was mostly oriented towards 90° with Iguana grade control oriented towards 45°.</li> <li>• Drilling of laterite mineralisation is almost exclusively vertical in nature.</li> </ul> <p>The Iguana Deposit presents multiple orientations of mineralisation which include both near vertical sets and shallow dipping mineralisation zones.</p>

CRITERIA	JORC CODE EXPLANATION	COMMENTARY
		<ul style="list-style-type: none"> <li>• Drilling in the Iguana region has primarily been focused on -60° dipping holes, either East or West orientated. Recent drilling by Beacon Minerals replicated prior RC drilling orientations in the region.</li> <li>• The narrowest orientation of the orezone is its east-west extents. In addition though many different mineralised orientations are present, they are predominantly steep in angle facilitating east and west orientation drilling being the most suitable approach for mineralisation defining.</li> </ul>
<b>Sample security</b>	<i>The measures taken to ensure sample security.</i>	Unknown for all drilling except for the following: <ul style="list-style-type: none"> <li>• Monarch: Sample calicos were placed into numbered plastic bags and cable tied. Any samples going to SGS were collected daily by the lab. Samples sent to ALS were placed into sample crates and sent via courier on a weekly basis.</li> <li>• EGL: Samples were bagged, tied and in a secure yard. Once submitted to the laboratories they are stored in cages within a secure fenced compound. Samples are tracked through the laboratory via their LIMS.</li> <li>• OBM: Samples were bagged, tied and stored in a secure yard on site. Once submitted to the laboratories they were stored in cages within a secure fenced compound. Samples are tracked through the laboratory via their LIMS.</li> <li>• Beacon Minerals: Samples were collected from the field and immediately recorded, and dispatched to BV Cunningham utilising Beacon employees or appropriately qualified contractors</li> </ul>
<b>Audits or reviews</b>	<i>The results of any audits or reviews of sampling techniques and data.</i>	OBM has reviewed historical digital data, particularly from the Iguana deposit, and compared it to hardcopy and digital (including WAMEX) records.

**Section 2: Reporting of Exploration Results**

Criteria	JORC Code explanation	Commentary
<b>Mineral tenement and land tenure status</b>	<p><i>Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings.</i></p> <p><i>The security of the tenure held at the time of reporting along with any known impediments to obtaining a licence to operate in the area.</i></p>	<p>The Lady Ida Project consist of M16/262 (the Iguana Deposit is located on M16/262), M16/263, M16/264, L15/224, L16/58, L16/62, L16/103, L16/138 and application L16/142 which is the ground the subject of the Earn-In, JV and Tenement Transfer Agreement between the Company, Beacon Mining Pty Ltd, Lamerton Pty Ltd and Geoda Pty Ltd.</p>
<b>Exploration done by other parties</b>	<p><i>Acknowledgment and appraisal of exploration by other parties.</i></p>	<p>Drilling, sampling and assay procedures and methods as stated in the database and confirmed from WAMEX reports and hardcopy records are considered acceptable and to industry standards of the time. There is sufficient understanding of drilling, sampling and assay methodologies for the majority of drilling in the Lady Ida area. BCN is confident that previous operators completed work to standards considered acceptable for the time.</p>
<b>Geology</b>	<p><i>Deposit type, geological setting and style of mineralisation.</i></p>	<p>The project is located along the inferred trace of the Ida Fault, a north-south trending deep-seated crustal structure juxtaposing batholithic granites and subordinate basalt and banded iron formation of the Southern Cross Province against greenstones of the Eastern Goldfields Province.</p> <p>The Eastern Goldfields Province sequences are metamorphosed to amphibolite facies and dominated by tholeiitic to komatiitic basalts, tremolite-chlorite rich ultramafics and psammitic to pelitic sediments. The regional stratigraphy trends north-northwest, sub-parallel to the Ida Fault, and the regional dip is sub-vertical. The structural complexity of the area, including inferred thrusts, fault splays and crosscutting shears, presents good potential for additional trap sites.</p> <p>The resource at Iguana is dominantly hosted in a highly sheared, silica-muscovite-carbonate altered, tholeiitic metabasalt and sediments of lower to mid amphibolite facies. It is interpreted as being controlled by imbricate thrusts contained between two north-south trending faults. Ultramafic units lie to the west and the mafic-sedimentary package lies to the east. Post-mineralisation pegmatite dykes attain considerable thickness in places and stope out mineralisation.</p>
<b>Drillhole information</b>	<p><i>A summary of all information material to the understanding of the exploration results including a tabulation of the following information for all Material drillholes:</i></p> <ul style="list-style-type: none"> <li><i>easting and northing of the drillhole collar</i></li> <li><i>elevation or RL (Reduced Level – elevation above sea level in metres) of the drillhole collar</i></li> </ul>	<p>Refer to the collar information provided in this report for all Released RC Holes</p>

Criteria	JORC Code explanation	Commentary
	<ul style="list-style-type: none"> <li>dip and azimuth of the hole</li> <li>downhole length and interception depth</li> <li>hole length.</li> </ul>	
<b>Data aggregation methods</b>	<p><i>In reporting Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (e.g. cutting of high grades) and cut-off grades are usually Material and should be stated.</i></p> <p><i>Where aggregate intercepts incorporate short lengths of high grade results and longer lengths of low grade results, the procedure used for such aggregation should be stated and some typical examples of such aggregations should be shown in detail.</i></p> <p><i>The assumptions used for any reporting of metal equivalent values should be clearly stated.</i></p>	<p>Mineral intercepts are reported as raw, with no top cutting conducted.</p> <p>Mineral intercepts reported have an Au value greater than 0.5g/t. Internal dilution is restricted to 3m or less within intercept intervals.</p> <p>Metal equivalent calculations are not required as the Iguana project is gold only</p>
<b>Relationship between mineralisation widths and intercept lengths</b>	<p><i>These relationships are particularly important in the reporting of Exploration Results.</i></p> <p><i>If the geometry of the mineralisation with respect to the drillhole angle is known, its nature should be reported.</i></p> <p><i>If it is not known and only the down hole lengths are reported, there should be a clear statement to this effect (e.g. 'downhole length, true width not known').</i></p>	<p>Mineral intercepts have been recorded as downhole widths. The multiple different orientations of mineralisation present, with not all visually identifiable means an accurate true width is not possible.</p>
<b>Diagrams</b>	<p><i>Appropriate maps and sections (with scales) and tabulations of intercepts should be included for any significant discovery being reported These should include, but not be limited to a plan view of drillhole collar locations and appropriate sectional views.</i></p>	<p>See plan and cross-section views provided in this report.</p>
<b>Balanced reporting</b>	<p><i>Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/or widths should be practiced to avoid misleading reporting of Exploration Results.</i></p>	<p>Beacon Minerals is reporting only significant intercepts as prior outlined (greater than 0.5g/t zone, with less than 3m of internal dilution). All drillhole zones not tabularised in this report can be interpreted as being insignificant in relation to Au grades.</p>
<b>Other substantive exploration data</b>	<p><i>Other exploration data, if meaningful and material, should be reported including (but not limited to): geological observations; geophysical survey results; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances.</i></p>	<p>Iguana has no known reported metallurgical issues. Primary ore was previously mined by Delta in the early 2000s with ore treated at the Greenfields processing plant in Coolgardie. Recovery and reconciliation figures are unknown.</p>
<b>Further work</b>	<p><i>The nature and scale of planned further work (e.g. tests for lateral extensions or depth extensions or large-scale step-out drilling).</i></p>	<p>Further resource work is ongoing, with new data currently being incorporated into an updated resource model.</p>

Criteria	JORC Code explanation	Commentary
	<i>Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive.</i>	